



Single-test evaluation of directional elastic properties of anisotropic structured materials

Jagannadh Boddapati ^{a,1}, Moritz Flaschel ^{b,1}, Siddhant Kumar ^c, Laura De Lorenzis ^b, Chiara Daraio ^{a,*}

^a Division of Engineering and Applied Science, California Institute of Technology, Pasadena, CA 91125, USA

^b Department of Mechanical and Process Engineering, ETH Zürich, 8092 Zürich, Switzerland

^c Department of Materials Science and Engineering, Delft University of Technology, 2628 CD Delft, The Netherlands

ARTICLE INFO

Keywords:

Anisotropy
Shear-normal coupling
Virtual fields method
Metamaterial design
Data-driven identification
Inverse problems

ABSTRACT

When the elastic properties of structured materials become direction-dependent, the number of their descriptors increases. For example, in two-dimensions, the anisotropic behavior of materials is described by up to 6 independent elastic stiffness parameters, as opposed to only 2 needed for isotropic materials. Such high number of parameters expands the design space of structured materials and leads to unusual phenomena, such as materials that can shear under uniaxial compression. However, an increased number of properties descriptors and the coupling between shear and normal deformations render the experimental evaluation of material properties more challenging. In this paper, we propose a methodology based on the virtual fields method to identify six separate stiffness tensor parameters of two-dimensional anisotropic structured materials using just one tension test, thus eliminating the need for multiple experiments, as it is typical in traditional methods. The approach requires no stress data and uses full-field displacement data and global force data. We show the accuracy of our method using synthetic data generated from finite element simulations as well as experimental data from additively manufactured specimens.

1. Introduction

The advent of additive manufacturing has allowed the design and engineering of a new class of materials known as metamaterials, or structured/architected materials. Mechanical metamaterials are a special branch of metamaterials that derive special functionalities from their peculiar deformation, dynamic motion and/or elastic energy distribution (Lee et al., 2012; Christensen et al., 2015; Zadpoor, 2016; Bertoldi et al., 2017; Surjadi et al., 2019). Metamaterials derive their effective properties from both the micro- and meso-structure and their constitutive material properties. They often exhibit mechanical properties that deviate from those of their constituent materials, showing unusual behaviors, such as negative Poisson's ratios (Greaves et al., 2011), vanishing shear moduli (Kadic et al., 2012), and negative refractive indices (Kaina et al., 2015).

By carefully selecting the geometry of the micro- and meso-structures with varying symmetries (Milton and Cherkaev, 1995; Kadic et al., 2012; Wu et al., 2019; Kulagin et al., 2020; Mao et al., 2020; Bastek et al., 2022), metamaterial designers can explore novel anisotropy classes in the material responses. In turn, the presence of rich anisotropy expands the materials' functionality space, by exploiting coupled-deformation mechanisms that are non-existent in symmetric structures. Examples include metamaterials that

* Corresponding author.

E-mail address: daraio@caltech.edu (C. Daraio).

¹ These authors contributed equally.

twist under compression (Frenzel et al., 2017; Chen et al., 2018; Wu et al., 2019; Yuan et al., 2021), shear under thermal loading (Ni et al., 2019) and shape-morph (Guseinov et al., 2020; Risso et al., 2021; Agnelli et al., 2022). In the dynamic regime, anisotropy allows observing phenomena like conical refraction (Ahn et al., 2017) and control of broadband elastic waves (Zheng et al., 2019; Yang et al., 2019; Zheng et al., 2020).

In a two-dimensional continuum, the elastic behavior of an anisotropic material is described using six independent elastic parameters (Ting and Chi-Tsai, 1996). In experiments, characterizing these many independent elastic parameters is quite complex. Indeed, the presence of shear-normal coupling makes it hard to measure even one of the six parameters from a single experiment. Prior work suggested different approaches to experimentally measure the elastic parameters for different anisotropy classes (Schittny et al., 2013; Considine et al., 2014; Gras et al., 2015; Lee et al., 2016; Kim et al., 2020; Agnelli et al., 2021). However, most of these approaches focus on measuring the stiffness tensor components when the off-diagonal, shear-normal coupling, components are absent. In addition, several of these approaches require multiple experimental steps. For example, techniques based on the detection of different acoustic wave speeds along different material directions involve multiple tests and assume a certain material symmetry in predicting elastic parameters (Every and Sachse, 1990; François et al., 1998). To date, there are no experimental methods that can measure the stiffness parameters of fully anisotropic structured materials from a single experiment.

Traditional material parameter identification methods rely on single-load experimental setups with homogeneous (constant) strain distributions within the tested specimen, which allow the derivation of closed-form stress-strain relations. However, the amount of data that can be acquired through a one dimensional tension test, for example, is limited (e.g., one stress-strain data pair for each measurement). When characterizing complex materials, multiple experimental setups with different loading conditions are needed. Full-field identification methods allow extracting additional information from single-load experiments. Measuring the full displacement field, e.g., through Digital Image Correlation (DIC), of arbitrarily shaped specimens under loading maximizes the amount of data generated from a single experimental test. Such data can then be used to characterize the material by applying inverse identification methods such as, among others, Finite Element Model Updating, the Equilibrium Gap Method or the Virtual Fields Method (VFM), see Avril et al. (2008), Roux and Hild (2020), Pierron (2023) for a review.

These methods have in common that they are used to calibrate the parameters of an a priori chosen material model, i.e., the mathematical functions and operations that describe the material response need to be fixed by means of the intuition or modeling experience of the user. However, the selection of inappropriate a priori assumptions about the model and its underlying mathematical structure can introduce errors. Recent research used full-field data to train machine-learning-models, whose versatile ansatz spaces promise to mitigate modeling errors. Flaschel et al. (2021), for example, proposed the method EUCLID (Efficient Unsupervised Constitutive Law Identification and Discovery) that uses sparse regression (Tibshirani, 1996) informed by full-field displacement data and net reaction force data, to automatically select interpretable material models from a potentially large predefined set of candidate material models. EUCLID has been applied to hyperelasticity (Flaschel et al., 2021), elastoplasticity (Flaschel et al., 2022), viscoelasticity (Marino et al., 2023), and generalized standard materials (Flaschel et al., 2023), see Flaschel (2023) for an overview. Further, EUCLID was formulated in a Bayesian setting by Joshi et al. (2022) to simultaneously perform model selection and quantification of uncertainty in the material parameters. In contrast to selecting interpretable material models through sparse regression, full-field data may also be used to train black-box material model surrogates like neural networks, as shown by Man and Furukawa (2011), Huang et al. (2020), Liu et al. (2020) for small strain elasticity and by Thakolkaran et al. (2022) for hyperelasticity. In the present work, it is assumed that the material response does not leave the realm of elasticity at infinitesimal strains. Thus, the material model can be assumed to be known a priori, and its parameters are calibrated with the VFM.

The VFM, originally proposed by Grédiac (1989) (see also Grédiac et al., 2008; Pierron and Grédiac, 2012), employs the balance of linear momentum in its weak form, to identify unknown material parameters. The VFM method assumes that the kinematic fields in the specimen, as well as the reaction forces at the boundaries, are known from experiments. As such, material parameters remain the only unknowns in the balance equations and can be calculated using standard linear or nonlinear solvers. In essence, the VFM describes the inverse problem to the classical Finite Element Method (FEM). The method has been applied in various cases, such as small-strain elasticity, elasto-plasticity (Grédiac and Pierron, 2006), and hyperelasticity (Promma et al., 2009), among others.

The accuracy of the VFM in identifying unknown material parameters and its sensitivity to noise is highly dependent on the choice of the functions for which the weak linear momentum balance is tested, also known as the virtual displacement fields. A distinction can be made between *global* virtual fields that are defined over the whole specimen domain, such as polynomials, and *local* virtual fields with compact support, such as in the Bubnov-Galerkin discretization with piecewise polynomial shape functions. As the choice of the virtual fields is arbitrary and user-dependent, several attempts have been made to automate and optimize it (Avril et al., 2004; Pierron et al., 2010; Marek et al., 2017).

In this article, full-field measurement based identification, and in particular the VFM, is explored in the context of anisotropic structured materials and compared to traditional identification methods. We focus in particular on the identification of shear-normal coupling parameters, notoriously complex to extract from conventional experiments. The rest of the paper is organized as follows. In Section 2, we discuss the theory of anisotropic linear elasticity and introduce our model setup used for parameter identification. In Section 3, we present our virtual fields method. In Section 4, we describe our experimental and numerical data acquisition methods. In Section 5, we discuss our results, including experimental validation, and we draw our conclusions in Section 6.

2. Material model and geometry

In this section, we review the fundamental equations of linear elasticity at infinitesimal strains and introduce our model setup used to identify the governing material parameters of anisotropic metamaterials.

2.1. Anisotropic linear elasticity

Under the small strain assumption, the constitutive law for a general anisotropic solid, which relates the Cauchy stress tensor σ and the infinitesimal strain tensor ϵ , is given by the generalized Hooke's law (Rychlewski, 1984; Ting and Chi-Tsai, 1996),

$$\sigma = C\epsilon \quad \text{or} \quad (\sigma_{ij} = C_{ijkl}\epsilon_{kl}), \quad (1)$$

where C is a fourth-order tensor, known as the elasticity tensor or the stiffness tensor, and Einstein's notation for summation over repeated indices is followed. For a two-dimensional anisotropic solid, under plane stress conditions, Eq. (1) can be written using Voigt notation as

$$\begin{bmatrix} \sigma_{11} \\ \sigma_{22} \\ \sigma_{12} \end{bmatrix} = \begin{bmatrix} C_{1111} & C_{1122} & C_{1112} \\ C_{1122} & C_{2222} & C_{2212} \\ C_{1112} & C_{2212} & C_{1212} \end{bmatrix} \begin{bmatrix} \epsilon_{11} \\ \epsilon_{22} \\ 2\epsilon_{12} \end{bmatrix}, \quad (2)$$

where C_{1111} , C_{1122} , C_{2222} , C_{1112} , C_{2212} , C_{1212} are the elasticity tensor parameters in a given reference frame, ϵ_{11} , ϵ_{22} are the axial strains, ϵ_{12} is the shear strain, σ_{11} , σ_{22} are the axial stresses, and σ_{12} is the shear stress. For readability, we combine the pair of indices as follows: $0_{11} \rightarrow 0_1$, $0_{22} \rightarrow 0_2$, $0_{12} \rightarrow 0_6$ and write Eq. (2) as

$$\begin{bmatrix} \sigma_1 \\ \sigma_2 \\ \sigma_6 \end{bmatrix} = \begin{bmatrix} C_{11} & C_{12} & C_{16} \\ C_{12} & C_{22} & C_{26} \\ C_{16} & C_{26} & C_{66} \end{bmatrix} \begin{bmatrix} \epsilon_1 \\ \epsilon_2 \\ 2\epsilon_6 \end{bmatrix}. \quad (3)$$

Our objective is to identify these six material parameters C_{11} , C_{12} , C_{22} , C_{16} , C_{26} , C_{66} from experimental measurements while fulfilling certain constraints. From thermodynamic constraints, the elasticity tensor has to be positive definite, which implies

$$C_{11} > 0, \quad C_{22} > 0, \quad C_{66} > 0, \quad (4a)$$

$$C_{11}C_{22} - C_{12}^2 > 0, \quad C_{11}C_{66} - C_{16}^2 > 0, \quad C_{22}C_{66} - C_{26}^2 > 0. \quad (4b)$$

The stiffness parameter C_{12} represents the extension-to-extension deformation coupling. The stiffness parameters C_{16} , C_{26} represent the extension-to-shear coupling, also known as shear-normal coupling, which induces shear stress from axial strains, and axial stresses from shear strains. Shear-normal coupling has been explored in the context of structured materials by Karathanasopoulos et al. (2020), Dos Reis and Karathanasopoulos (2022). As a result of these anisotropy-induced couplings, the experimental identification of the material parameters becomes non-trivial because a constant state of strain is hard to achieve, even in a standard uniaxial tension test.

Note that the parameters C_{16} and C_{26} will be zero if the material has symmetry planes along the x_1 and x_2 axes. Thus, the existence of shear-normal coupling and the maximum number of independent stiffness tensor parameters depend on the symmetries associated with the material microscopic topology (Ting and Chi-Tsai, 1996; Podestá et al., 2019). In plane elasticity, stiffness tensors are categorized into four symmetry classes. They are denoted as $O(2)$ for Isotropic, D_4 for Tetragonal, D_2 for Orthotropic and Z_2 for Digonal (fully anisotropic) with 2, 3, 4 and 6 independent parameters respectively. This categorization is based on the invariants of the stiffness tensor (Forte and Vianello, 2014; Auffray and Ropars, 2016). However, in our methods of parameter identification, we do not consider any prior information on the material symmetries or the number of independent material parameters.

2.2. Model setup

Without loss of generality, we study two-dimensional structured solids, obtained from finite periodic tessellation of square unit cells (Fig. 1).² We focus on identifying the effective anisotropic material parameters of these composite assemblies, as linear elastic continua.

To design unit cells, we follow an approach inspired by Cahn's method of generating Gaussian random fields by superposing plane waves of fixed wavelength but random in phase and direction (Cahn, 1965; Soyarslan et al., 2018; Kumar et al., 2020). We first define a function $f(x_1, x_2)$, as a linear superposition of cosine periodic functions:

$$f(x_1, x_2) = \sum_{m,n} A_{mn} \cos(2\pi(mx_1 + nx_2)), \quad \forall (x_1, x_2) \in [-0.5, 0.5], \quad \forall m, n \in [-3, -2, -1, 0, 1, 2, 3], \quad (5)$$

where m, n are spatial frequencies, and A_{mn} are the corresponding cosine function weights. The function is then thresholded at a value ξ , to generate a binary image which represents a unit cell, as shown in Fig. 1, panels a, b. Each unit cell is pixelated and discretized with a 100×100 square mesh. In this pixelated representation, the gray phase represents a stiffer material and the black phase represents a softer material (see Section 4.3.1).

The periodicity is ensured from the choice of the cosine functions directly. We randomly sample the weights A_{mn} and the threshold value ξ to generate a small database of unit cells (about 100), from which we pick four unit cells to study in this paper. The four unit cells are chosen such that they are diverse in anisotropic properties and suitable for additive manufacturing (see Section 4.1).

² Our methods are easily extendable to non-square unit cells.

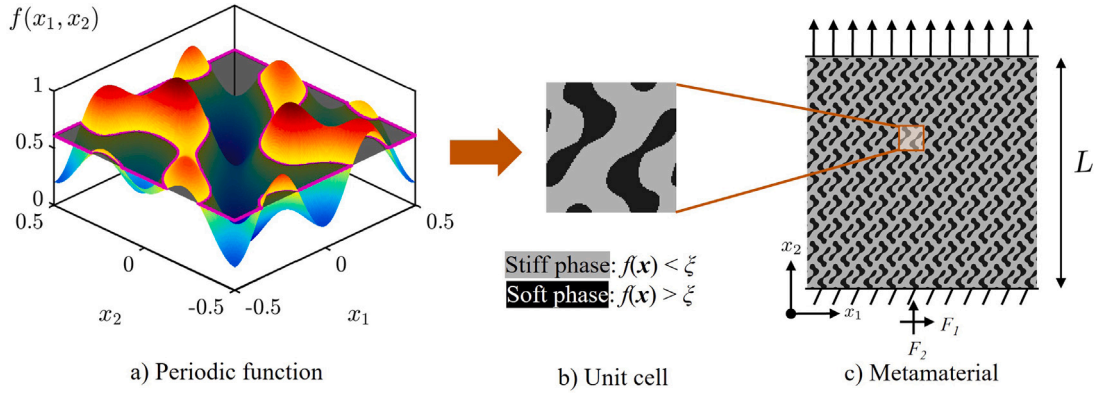


Fig. 1. (a) Design of an anisotropic unit cell geometry by thresholding a periodic function $f(x_1, x_2)$. (b) A two-phase unit cell geometry consisting of a stiffer (gray) and a softer phase (black). (c) A two-dimensional anisotropic metamaterial created by tessellating the unit cell geometry (shown in the inset) ten times along both x_1 - and x_2 -axes.

We consider a unit cell as suitable for manufacturing if the stiff phase is connected in the finite periodic tessellation with a minimum feature size of 5 pixels, matching the resolution of our chosen additive manufacturing approach.

A schematic of our setup is shown in Fig. 1c. A two-dimensional square anisotropic structured solid with 10×10 unit cell tessellation, with side length L , is subjected to a displacement-controlled tension test. The boundary conditions are such that the bottom end is fixed, while a displacement of $\mathbf{u} = [0, u_p]^T$ is prescribed at the top end. The reaction force components measured at the fixed end are denoted as F_1, F_2 .

3. Virtual fields method for anisotropic metamaterials

Many parameter identification methods rely on conducting multiple experiments, which are time consuming, complex and require specialized equipment. To circumvent these drawbacks, we explore a material characterization method based on the VFM that solely relies on full-field displacements and net reaction force measurements from a single experimental test. In this section, after discussing the assumptions underlying the adoption of the VFM for metamaterials, we outline all the components of the proposed method.

3.1. Basic assumptions

The VFM (Grédiac, 1989; Grédiac et al., 2008; Pierron and Grédiac, 2012) exploits the weak formulation of linear momentum balance, i.e., the principle of virtual work, as a constraint on the material parameter space. Since the full displacement field over the specimen and the net reaction forces at the specimen boundaries are known, testing the weak formulation for a suitable set of test functions (also known as virtual fields) results in a system of equations that can be solved for the unknown material parameters. By choosing the test functions as not constant in space, the linear momentum balance is tested in different regions of the considered specimen domain. As such, the VFM takes advantage of the local strain data, as opposed to global methods for parameter identification.

In the following, the VFM is used to characterize the mechanical behavior of metamaterials. However, it should be noted that – due to the non-homogeneous nature of the metamaterials – the application of identification methods based on full-field measurements is not trivial. Full-field measurement techniques such as DIC measure the kinematic fields locally, i.e., at several points on the considered specimen surface. The studied metamaterials are not expected to behave at these local points as their homogenized counterparts, especially when the number of repeating unit cells is low in comparison to the size of the specimen. To give an example, in Section 5.1.1 the deformation of a heterogeneous metamaterial specimen will be compared to that of an equally-dimensioned homogeneous body, whose stiffness is set to the homogenized stiffness of the metamaterial. Under the same loading conditions, the two specimens exhibit different local displacements, which is likely caused by local size effects and the different boundary conditions that are assumed during the loading of the macroscopic structure and the homogenization of the microscopic unit cell. It is observed that deviations between the kinematic fields are predominant at the boundary and in particular at the corners of the domain. This agrees with theoretical studies on heterogeneous metamaterials, which suggest the usage of non-local – e.g., higher-order strain-gradient based – theories as proposed by Mindlin and Eshel (1968), to model size effects and wedge forces appearing at corners of non-homogeneous bodies (Fischer et al., 2011; Andraus et al., 2016; Yang et al., 2021). Within this work, such theories are avoided for the sake of simplicity and to keep a reasonably low number of material parameters. Hence, the assumption is made that the global material behavior of the metamaterials can be characterized based on local kinematic measurements within a local constitutive theory. As we will see later, this assumption will introduce errors in the identification procedure, which are, however, below a practically relevant level. During the development of the VFM, we found that the locally measured kinematic data must be treated with care, especially at the boundary and the corners of the specimen. We will later

introduce specifically designed virtual fields that reduce the influence of data acquired at the specimen boundary and corners (see Section 3.5 for details).³

3.2. Required data

To identify the unknown parameters, the VFM needs diverse local strain data, i.e., strain fields that are not homogeneous. Therefore, data that serve as input for the VFM are usually generated by testing complex specimen geometries under complex loading conditions (Kim et al., 2014; Rossi et al., 2015). However, for the structured materials considered in this study, generating complex specimen geometries (e.g., a plate with holes or notches) and studying their behavior under complex loading conditions is not trivial. Local features like holes or notches may lead to stress concentrations or singularities and hence more complex geometries may be prone to behave locally inelastic or even fail. Further, we will show later that the VFM performs best if we do not feed the method with data at the boundary of the specimen. Introducing more features like holes or notches to the geometry would increase the boundary and thus reduce the amount of data suitable to be used by the VFM.

For our purposes we will show that, due to the anisotropy of the material, a clamped square plate under uniaxial tension produces a sufficiently heterogeneous strain field. We hence consider a displacement-controlled uniaxial tension experiment of a square-shaped specimen that consists of $n_c \times n_c$ repeating square unit cells of the considered metamaterial (Fig. 1). At the fixed boundary of the specimen, a load cell measures the net reaction force. Further, the full-field deformation of the specimen is tracked through DIC, which measures the local displacements of the solid material. After preprocessing the data, the VFM takes as input the displacement measurements at the $(n_c + 1) \times (n_c + 1)$ unit cell corners and the net reaction forces. A quadrilateral finite element mesh is generated such that each of the $n_c \times n_c$ elements corresponds to one unit cell and the element nodes correspond to the unit cell corners with experimentally known displacement values. The continuous displacement field $\mathbf{u}(\mathbf{x})$ is hence approximated by

$$\mathbf{u}(\mathbf{x}) = \sum_{a=1}^{n_n} N^a(\mathbf{x}) \mathbf{u}^a, \quad (6)$$

where $n_n = (n_c + 1)^2$ denotes the number of nodes in the finite element mesh and \mathbf{u}^a are the known nodal displacements, while $N^a(\mathbf{x})$ are the standard ansatz functions of bilinear quadrilateral finite elements. The infinitesimal strain field is then obtained as the symmetric gradient of the displacement field, i.e., $\boldsymbol{\varepsilon}(\mathbf{x}) = \frac{1}{2} (\nabla \mathbf{u}(\mathbf{x}) + (\nabla \mathbf{u}(\mathbf{x}))^T)$.

3.3. Weak formulation of linear momentum balance

We denote the specimen domain and its boundary as Ω and $\partial\Omega$, respectively, and the surface traction force acting on $\partial\Omega$ as \mathbf{t} . Assuming no inertia and body forces, the weak form of linear momentum balance reads

$$\int_{\Omega} \boldsymbol{\sigma}(\mathbf{x}) : \nabla \mathbf{v}(\mathbf{x}) \, dA - \int_{\partial\Omega} \mathbf{t} \cdot \mathbf{v}(\mathbf{x}) \, ds = 0, \quad (7)$$

which has to hold true for all admissible, i.e., sufficiently regular, test functions $\mathbf{v}(\mathbf{x})$. Note that we are not introducing the classical distinction between Dirichlet and Neumann portions of the boundary; accordingly, we are not requiring admissible test functions to vanish anywhere.

3.4. Discretization

The weak form of linear momentum balance has to hold true for any chosen set of admissible test functions. Here, we adopt the standard (Bubnov–Galerkin) approach and express the test functions as a linear combination of the same shape functions $N^a(\mathbf{x})$ used to interpolate the displacement data

$$\mathbf{v}(\mathbf{x}) = \sum_{a=1}^{n_n} N^a(\mathbf{x}) \mathbf{v}^a. \quad (8)$$

Inserting the test function ansatz into the weak form of linear momentum balance results in

$$\sum_{a=1}^{n_n} \mathbf{v}^a \cdot \left[\underbrace{\int_{\Omega} \boldsymbol{\sigma} \nabla N^a(\mathbf{x}) \, dA}_{\mathbf{F}_{\text{int}}^a} - \underbrace{\int_{\partial\Omega} \mathbf{t} N^a(\mathbf{x}) \, ds}_{\mathbf{F}_{\text{ext}}^a} \right] = 0, \quad (9)$$

where the first and second integral are the nodal internal forces $\mathbf{F}_{\text{int}}^a$ and nodal external forces $\mathbf{F}_{\text{ext}}^a$, respectively. By employing the constitutive relation Eq. (3), the nodal internal forces may be written as

$$\mathbf{F}_{\text{int}}^a = \int_{\Omega} \boldsymbol{\sigma} \nabla N^a \, dA,$$

³ We note at this point that reducing the influence of data acquired at the specimen boundary and corners may be beneficial not only when studying heterogeneous materials. Even for homogeneous specimens, the acquisition of kinematic data at the specimen boundary via DIC is known to be difficult.

$$\begin{aligned}
 &= \int_{\Omega} \begin{bmatrix} \sigma_1 N_{,x}^a + \sigma_6 N_{,y}^a \\ \sigma_6 N_{,x}^a + \sigma_2 N_{,y}^a \end{bmatrix} dA, \\
 &= \int_{\Omega} \begin{bmatrix} C_{11}\epsilon_1 N_{,x}^a + C_{12}\epsilon_2 N_{,x}^a + 2C_{16}\epsilon_6 N_{,x}^a + C_{16}\epsilon_1 N_{,y}^a + C_{26}\epsilon_2 N_{,y}^a + 2C_{66}\epsilon_6 N_{,y}^a \\ C_{16}\epsilon_1 N_{,x}^a + C_{26}\epsilon_2 N_{,x}^a + 2C_{66}\epsilon_6 N_{,x}^a + C_{12}\epsilon_1 N_{,y}^a + C_{22}\epsilon_2 N_{,y}^a + 2C_{26}\epsilon_6 N_{,y}^a \end{bmatrix} dA, \\
 &= \int_{\Omega} \begin{bmatrix} \epsilon_1 N_{,x}^a & \epsilon_2 N_{,x}^a & 0 & 2\epsilon_6 N_{,x}^a + \epsilon_1 N_{,y}^a & \epsilon_2 N_{,y}^a & 2\epsilon_6 N_{,y}^a \\ 0 & \epsilon_1 N_{,y}^a & \epsilon_2 N_{,y}^a & \epsilon_1 N_{,x}^a & \epsilon_2 N_{,x}^a + 2\epsilon_6 N_{,y}^a & 2\epsilon_6 N_{,x}^a \end{bmatrix} dA \mathbf{C}_{\text{vec}}, \tag{10}
 \end{aligned}$$

where the elasticity tensor parameters $\mathbf{C}_{\text{vec}} = [C_{11} \ C_{12} \ C_{22} \ C_{16} \ C_{26} \ C_{66}]^T$ are assumed to be constant in space.

3.5. Choice of test functions

Choosing a test function in the form of (8) and evaluating (9) results in two linear equations with the material parameters as unknowns. As the weak linear momentum balance has to hold true for any test function this provides an infinite supply of linear equations. Hence, the problem at hand is overdetermined and different choices of test functions will yield different solutions for the unknown material parameters.

As discussed in Section 3.1, the deformation of a heterogeneous specimen and that of its homogenized counterpart under the same loading conditions are locally different, a phenomenon that is best observed at the boundary and at the corners of the specimen where local effects are especially pronounced. In the following, this special characteristic of the problem at hand motivates a special choice of the test functions that avoids evaluations of the linear momentum balance in the boundary regions of the specimen.

First, we define test functions that are constant at the nodes corresponding to one finite element, i.e., one unit cell, and zero at all other nodes. To this end, we define $C = \{1, \dots, n_c^2\}$ as the set of all unit cells and D^c as the set of all nodes corresponding to the unit cell $c \in C$, and define a set of test functions as

$$\mathcal{V} = \left\{ \mathbf{v}(\mathbf{x}) = \frac{1}{n_{nc}} \sum_{a \in D^c} N^a(\mathbf{x}) \mathbf{e}_i \mid c \in C, i \in \{1, 2\} \right\}, \tag{11}$$

where \mathbf{e}_i are the unit vectors in the corresponding x - and y -direction. Note that the test functions are normalized by dividing by the number of nodes corresponding to the unit cell n_{nc} (equal to 4 in our case).

Using the test functions in \mathcal{V} to test weak linear momentum balance would cause two problems. First, at elements adjacent to the loaded and to the restrained portions of the boundary, the external force contributions F_{ext}^a in (9) are unknown, leading to equations that could not be solved for the unknown material parameters. And second, we want to avoid using data at the specimen boundary due to the reasons discussed earlier. Therefore, we modify (11) such that

$$\mathcal{V}^{\text{int}} = \left\{ \mathbf{v}(\mathbf{x}) = \frac{1}{n_{nc}} \sum_{a \in D^c} N^a(\mathbf{x}) \mathbf{e}_i \mid c \in C^{\text{int}}, i \in \{1, 2\} \right\}, \tag{12}$$

where $C^{\text{int}} \subset C$ denotes a reduced set of unit cells that does not include unit cells close to the boundary. We found that ignoring two rows of unit cells at the top and bottom boundary as well as two columns of unit cells at the left and right boundary are a good compromise, and we kept this choice constant throughout all tests. As the fields in \mathcal{V}^{int} depend on \mathbf{e}_i , each field is zero in either x - or y -direction. The non-zero component of an exemplary virtual field in \mathcal{V}^{int} is shown in Fig. 2 (left).

Evaluating Eq. (9) for this set of functions leads to

$$\frac{1}{n_{nc}} \sum_{a \in D^c} F_{\text{int}}^a = \mathbf{0}, \quad \forall c \in C^{\text{int}}. \tag{13}$$

Hence, this choice of virtual fields can be interpreted physically as enforcing that the sum of internal forces over one unit cell should vanish.

Eqs. (13) are not sufficient to identify the unknown material parameters, as the trivial solution $\mathbf{C}_{\text{vec}} = \mathbf{0}$ fulfills (13). To obtain a well-posed problem, the measured reaction forces need to be incorporated. At the same time, we want to avoid using displacement data at the specimen boundary. Therefore, we consider the free-body diagram of the lower half of the domain as depicted in Fig. 2 (right). Denoting the half-body domain as $\Omega^* = \{\mathbf{x} \mid 0 \leq x_1 \leq L, \ 0 \leq x_2 \leq \frac{L}{2}\}$ and its boundary as $\partial\Omega^*$, the weak form of linear momentum balance for this domain reads

$$\int_{\Omega^*} \boldsymbol{\sigma}(\mathbf{x}) : \nabla \mathbf{v}(\mathbf{x}) \, dA - \int_{\partial\Omega^*} \mathbf{t} \cdot \mathbf{v}(\mathbf{x}) \, ds = 0. \tag{14}$$

Inserting the test function ansatz leads to

$$\sum_{a=1}^{n_n} \mathbf{v}^a \cdot \left[\underbrace{\int_{\Omega^*} \boldsymbol{\sigma} \nabla N^a(\mathbf{x}) \, dA}_{\mathbf{F}_{\text{int}}^{*a}} - \underbrace{\int_{\partial\Omega^*} \mathbf{t} N^a(\mathbf{x}) \, ds}_{\mathbf{F}_{\text{ext}}^{*a}} \right] = 0. \tag{15}$$

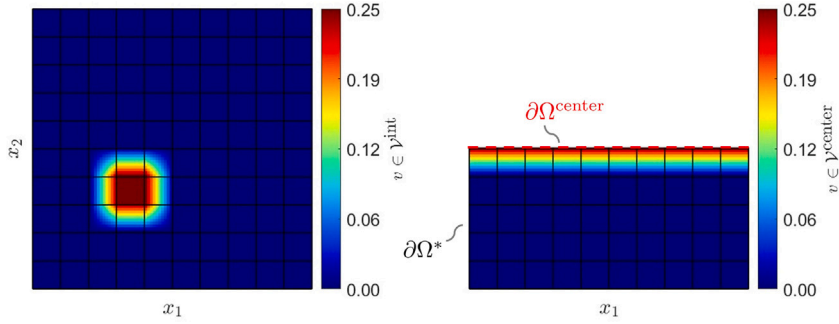


Fig. 2. Non-zero component of a virtual field in \mathcal{V}^{int} (left) and non-zero component of a virtual field in $\mathcal{V}^{\text{center}}$ (right).

We define $\mathcal{D}^{\text{center}} = \{a \mid y^a = \frac{L}{2}\}$ as the set of nodes in the center of the specimen. If the tessellated geometry consists of an odd number of unit cells in each spatial direction, i.e., there are no nodes at $y^a = \frac{L}{2}$, we consider instead $\mathcal{D}^{\text{center}} = \{a \mid y^a = \frac{L}{2} + \frac{L}{2n_c}\}$. We choose a set of virtual fields $\mathcal{V}^{\text{center}}$ that are constant along $\mathcal{D}^{\text{center}}$ and zero at all other nodes

$$\mathcal{V}^{\text{center}} = \left\{ \mathbf{v}(\mathbf{x}) = \frac{1}{n_{nc}} \sum_{a \in \mathcal{D}^{\text{center}}} N^a(\mathbf{x}) \mathbf{e}_i \mid i \in \{1, 2\} \right\}. \quad (16)$$

Evaluating (15) for these particularly chosen test functions results in

$$\sum_{a \in \mathcal{D}^{\text{center}}} \mathbf{F}_{\text{int}}^{*a} = \int_{\partial\Omega^{\text{center}}} \mathbf{t} \, ds = \mathbf{R}, \quad (17)$$

where $\partial\Omega^{\text{center}}$ is the top boundary of Ω^* . Note that due to the specific choice of the test functions, the surface integral simplifies in such a way that it equals the global reaction force \mathbf{R} , meaning that the sum of the internal forces at $\partial\Omega^{\text{center}}$ must equal the net reaction force.

3.6. Deterministic parameter identification

After choosing the virtual fields and considering (10), the linear equations in (13) can be assembled in a system of equations

$$\mathbf{A}^{\text{int}} \mathbf{C}_{\text{vec}} = \mathbf{0}, \quad (18)$$

and the linear equations in (17) can be rewritten as

$$\mathbf{A}^{\text{center}} \mathbf{C}_{\text{vec}} = \mathbf{R}, \quad (19)$$

where \mathbf{A}^{int} and $\mathbf{A}^{\text{center}}$ are in general non-symmetric matrices. The system formed by the linear Eqs. (18) and (19) is overdetermined, i.e., it consists of more equations than unknown parameters. Assuming that the equations in the overdetermined system are not linearly dependent (which is a valid assumption as every equation is perturbed by noise when considering experimental data), there is no unique solution that satisfies all equations. Instead, we obtain an approximate solution of the overdetermined system by minimizing the sum of squared residuals

$$\mathbf{C}_{\text{vec}}^{\text{opt}} = \arg \min_{\mathbf{C}_{\text{vec}}} (\|\mathbf{A}^{\text{int}} \mathbf{C}_{\text{vec}}\|^2 + \lambda_r \|\mathbf{A}^{\text{center}} \mathbf{C}_{\text{vec}} - \mathbf{R}\|^2), \quad (20)$$

where $\|\cdot\|$ is the Euclidean norm and $\lambda_r > 0$ is a weighting parameter that scales the different contributions to the minimization problem. As there are less equations in the system (19) than in (18), the weighting parameter should be chosen sufficiently larger than one ($\lambda_r \gg 1$). Following previous works (Flaschel et al., 2021, 2022, 2023), we choose $\lambda_r = 100$ and keep it constant throughout this work. Based on our experience, the choice of λ_r is not crucial for the success of the method (see also Joshi et al., 2022; Thakolkaran et al., 2022; Marino et al., 2023). The necessary condition for a minimum is

$$\bar{\mathbf{A}} \mathbf{C}_{\text{vec}}^{\text{opt}} = \bar{\mathbf{R}}, \quad \text{with} \quad \bar{\mathbf{A}} = (\mathbf{A}^{\text{int}})^T \mathbf{A}^{\text{int}} + \lambda_r (\mathbf{A}^{\text{center}})^T \mathbf{A}^{\text{center}}, \quad \bar{\mathbf{R}} = \lambda_r (\mathbf{A}^{\text{center}})^T \mathbf{R}, \quad (21)$$

which leads to a determined system of equations that can be solved for $\mathbf{C}_{\text{vec}}^{\text{opt}}$. The minimization problem in Eq. (20) can alternatively be written as

$$\mathbf{C}_{\text{vec}}^{\text{opt}} = \arg \min_{\mathbf{C}_{\text{vec}}} \|\mathbf{A} \mathbf{C}_{\text{vec}} - \mathbf{B}\|^2, \quad (22)$$

where we have defined

$$\mathbf{A} = \begin{bmatrix} \mathbf{A}^{\text{int}} \\ \sqrt{\lambda_r} \mathbf{A}^{\text{center}} \end{bmatrix}, \quad \mathbf{B} = \begin{bmatrix} \mathbf{0} \\ \sqrt{\lambda_r} \mathbf{R} \end{bmatrix}. \quad (23)$$

The necessary condition for a minimum then reads

$$\mathbf{A}^T \mathbf{A} \mathbf{C}_{\text{vec}}^{\text{opt}} = \mathbf{A}^T \mathbf{B}. \quad (24)$$

3.7. Bayesian inference

Besides the previously introduced deterministic approach, we further study the problem from a stochastic perspective. To this end, we construct a Bayesian linear regression model, for which we assume no intercept and a diffuse prior, as implemented in the Matlab® built-in function *bayeslm*.

We denote the number of rows in \mathbf{A} as n_{eq} and we define \mathbf{A}_i with $i \in \{1, \dots, n_{eq}\}$ as the i th row of \mathbf{A} . For each equation in the overdetermined system of equations $\mathbf{A} \mathbf{C}_{\text{vec}} = \mathbf{B}$, we assume the likelihood of obtaining B_i as a Gaussian likelihood with mean $\mathbf{A}_i \cdot \mathbf{C}_{\text{vec}}$ and standard deviation $\sigma > 0$, i.e.,

$$p(B_i | \mathbf{A}_i, \mathbf{C}_{\text{vec}}, \sigma^2) = \frac{1}{\sqrt{2\pi\sigma^2}} \exp \left[-\frac{(B_i - \mathbf{A}_i \cdot \mathbf{C}_{\text{vec}})^2}{2\sigma^2} \right], \quad (25)$$

where \mathbf{C}_{vec} and σ^2 are treated as random variables. Assuming further that the likelihoods are conditionally independent, we define the joint likelihood as

$$p(\mathbf{B} | \mathbf{A}, \mathbf{C}_{\text{vec}}, \sigma^2) = \prod_{i=1}^{n_{eq}} p_i(B_i | \mathbf{A}_i, \mathbf{C}_{\text{vec}}, \sigma^2). \quad (26)$$

Assuming here a diffuse prior for the joint prior distribution of \mathbf{C}_{vec} and σ^2 , i.e.,

$$p(\mathbf{C}_{\text{vec}}, \sigma^2) \propto \frac{1}{\sigma^2}, \quad (27)$$

the marginal posterior distributions of \mathbf{C}_{vec} and σ^2 are analytically tractable and implemented in the Matlab® function *bayeslm*.

4. Data acquisition

In this section, we first discuss the unit cell geometries considered for identification of the material parameters. Then, we describe our numerical and experimental data acquisition methods, including details on fabrication, experimental setup, testing and DIC.

4.1. Design and choice of unit cell geometries

We pick four unit cells with distinct/diverse effective stiffness tensor parameters (all with six non-zero stiffness parameters). Table 1 shows the unit cells along with their symmetry class and homogenized stiffness tensor. Geometry #1 has C_{22} as the largest stiffness parameter with C_{16} almost comparable to C_{12} and $C_{26} > C_{16}$. While geometry #2 has C_{11} as the largest stiffness parameter with $C_{16} > C_{26}$, geometry #3 has negative values for all of the off-diagonal parameters. Geometry #4 has four independent stiffness parameters with C_{66} as one of the largest values among other stiffness parameters, along with $C_{11} = C_{22}$ and $C_{16} = C_{26}$. The fill fraction of the stiff phase for all the unit cells lies between 60 and 70%.

4.2. Numerical data generation

Simulations: We use synthetic data generated using the FEM to verify our methods and aid our analysis before performing the experiments. Each pixel is discretized using a four-node plane-stress bilinear quadrilateral element. For tessellation, we vary the number of unit cells n_c between 5 and 25.





Homogenization: We compute the effective mechanical properties of the unit cells using the theory of homogenization implemented using the FEM (as in [Andreassen and Andreasen, 2014](#)).

4.3. Experimental data generation

4.3.1. Fabrication

As specimens with a large number of unit cells are difficult to fabricate, we here pick 10×10 tessellations to perform experimental validations. We use a commercial multi-material polyjet technology based 3D printer, Stratasys Objet500 Connex, to fabricate all the specimens. The dimensions of the specimen are $75 \times 75 \times 5$ mm excluding the portion that goes into the grips. We use Stratasys' proprietary material DM8530 for the stiff phase and TangoBlack for the soft phase. The material properties (DM8530: Young's modulus $E = 1000 \pm 90$ MPa and Poisson's ratio $\nu = 0.35$, TangoBlack: Young's modulus $E = 0.7$ MPa and Poisson's ratio $\nu = 0.49$) are experimentally measured following the ASTM D638-14 standard test method and the same values are used in the numerical computations.

Table 1
Unit cell geometries considered in this study along with their mechanical and symmetry properties.

Unit cell geometry	Name	Homogenized stiffness tensor (C^H) [MPa]	Elastic symmetry class
	Geometry #1	$\begin{bmatrix} 131.62 & 61.98 & 63.58 \\ 61.98 & 198.38 & 83.87 \\ 63.58 & 83.87 & 95.30 \end{bmatrix}$	Z_2
	Geometry #2	$\begin{bmatrix} 127.14 & 59.50 & 73.42 \\ 59.50 & 105.83 & 55.16 \\ 73.42 & 55.16 & 110.15 \end{bmatrix}$	Z_2
	Geometry #3	$\begin{bmatrix} 44.70 & -9.42 & -12.52 \\ -9.42 & 107.19 & -20.71 \\ -12.52 & -20.71 & 105.35 \end{bmatrix}$	Z_2
	Geometry #4	$\begin{bmatrix} 65.74 & 40.36 & 18.95 \\ 40.36 & 65.74 & 18.95 \\ 18.95 & 18.95 & 86.47 \end{bmatrix}$	D_2

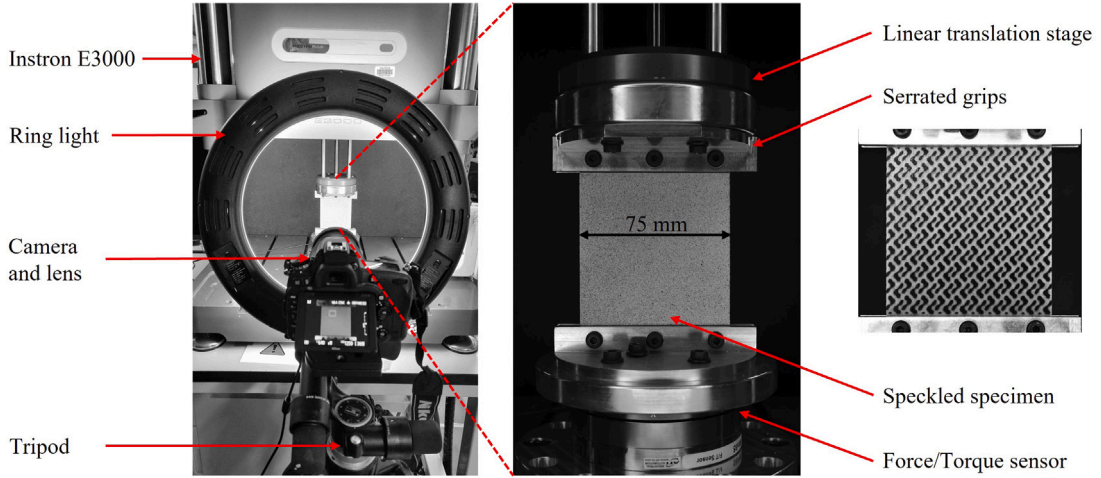


Fig. 3. Experimental setup for displacement-controlled uniaxial testing of an anisotropic metamaterial.

4.3.2. Experimental setup and testing

We subject the additively manufactured specimens to displacement-controlled tension tests using a universal testing machine, Instron E3000, mounted with a multi-axis force–torque sensor (ATI Mini85) as shown in Fig. 3. The force–torque sensor is acquired from ATI Industrial Automation. We apply a vertical displacement of 1.5 mm at the top boundary at a rate of 0.5 mm/min resulting in a global axial strain of $\bar{\epsilon}_{22} = 0.02$ and a global strain rate of $1.1 \times 10^{-4} \text{ s}^{-1}$. Custom-designed grips are fabricated out of aluminum and are serrated to hold the specimens firmly and prevent any lateral slipping. We use the same strain rate while measuring the constitutive material properties of the individual phases.

We use DIC, an image-based optical technique, to measure the full-field displacements (Sutton et al., 2009). We capture images at a frequency of 1 Hz using a Nikon D750 camera equipped with a Nikon AF-S NIKKOR 24-120 mm f/4G ED VR zoom lens. We use manual mode at an exposure rate of 1/640 s, an ISO setting of 1250 and an aperture setting of F8. The camera has a 6016 by 4016 square pixel resolution and the region of interest we studied is about 3060 by 3060 pixels. We place a ring light between the additively manufactured specimen and the camera to illuminate the surface uniformly and we place the camera lens at a distance of about 35–40 cm from the specimen plane.

4.3.3. Digital image correlation

Given a reference image f and a deformed image g , the correlation algorithm aims at minimizing the sum of squared differences over the considered domain Ω

$$\mathcal{T} = \int_{\Omega} (g(x + u(x)) - f(x))^2 dx, \quad (28)$$

where \mathbf{x} is the position in the reference image and $\mathbf{u}(\mathbf{x})$ is the displacement field which is interpolated as

$$\mathbf{u}(\mathbf{x}) = \sum u_n \phi_n(\mathbf{x}), \quad (29)$$

where ϕ_n are a set of shape functions and u_n the associated degrees of freedom. There are two approaches to determine the unknowns u_n , *local DIC* and *global DIC* (Hild and Roux, 2012). In the *local* approach, the region of interest (Ω) is divided into several sub-images known as subsets and the mean displacement of each subset is computed independently while minimizing the objective Eq. (28). In the *global* approach, shape functions defined through a finite element mesh over the whole region of interest are used (Besnard et al., 2006). The *global* approach assumes continuity of displacements over the entire region of interest which is well suited when the structure is heterogeneous. Moreover, the *global* approach provides the displacement information at the boundaries, which is hard to obtain using the *local* approach. The displacement data at the boundaries are an important input for the VFM. Hence, we follow the *global* approach to perform the correlation in this study.

We perform DIC using piece-wise linear shape functions defined on a triangular mesh to compute the displacements (as in Agnelli et al., 2021). We choose an edge length of 18 pixels (~ 0.44 mm) to construct the triangular mesh. We observe a noise floor of the order of 0.04 mm in the displacement data which is obtained from correlation performed on static images. In the future, experimental errors may be further reduced using the global DIC technique with quadratic interpolation (Blaysat et al., 2020). The data provided by the DIC correspond to the nodes that might not always align with the unit cell corners. To obtain the displacements of the unit cell corners, we further average the displacement data from the nodes that fall within 1 mm radius of a unit cell corner.

5. Results and discussion

In this section, we discuss the data generation from both numerical simulations and experiments. Afterwards, we apply the proposed deterministic parameter identification method to the data and discuss the results. Finally, at the end of the section, we apply the Bayesian method to the data.

5.1. Generation of full-field displacement data

5.1.1. Synthetic data

In the following, we investigate the synthetically generated displacement data for a heterogeneous structure in comparison to the computed displacement field of a homogeneous body, whose stiffness is equal to the homogenized stiffness of the heterogeneous structure. To simulate the displacement of a homogeneous body, we assume a 10×10 bilinear quadrilateral finite element mesh. The displacement of the heterogeneous body is computed on a much finer mesh with 1000×1000 elements. To allow for a comparison with the displacement field of the homogeneous body, the computed displacements at the unit cell corners of the heterogeneous body (i.e. the data of interest for the VFM) are extracted and interpolated with a bilinear polynomial for each unit cell. It can be seen in Fig. 4 that there is a good qualitative agreement between the two displacement fields for geometry #1 (see Fig. S1, Fig. S2 and Fig. S3 for the other geometries). However, there are quantitative differences due to local effects in the heterogeneous structure, which appear to be dominant at the boundary and corners of the specimen.

5.1.2. Comparison between experimental and synthetic data

In Fig. 5, we compare the full-field displacement and strain fields between the numerical and experimental data on the heterogeneous structure for geometry #1. (See Figs. S4 to S6 for the other geometries). We observe very good agreement between the numerical and experimental data, especially for the variables u_2, ϵ_{22} . However, the experimentally measured u_1 appears to be slightly higher than the numerical data, by about 0.1 mm, for all the geometries. Also the two ϵ_{11} fields are in good qualitative agreement, but experimental strains are larger. As expected, most of the strain is localized in the softer phase, although the applied global strain ($\bar{\epsilon}_{22}$) is 0.02.

Further, a comparison of the displacement fields after postprocessing the synthetic and experimental data, i.e., after extracting and interpolating the displacements at the unit cell corners for all the geometries are shown in Fig. S7, Fig. S8, Fig. S9, and Fig. S10. All displacements are in good agreement. An exception is observed for geometry #3 (see Fig. S5 and Fig. S9), for which the experimentally measured horizontal displacement u_1 does not compare well to the corresponding finite element results. The unit cell architecture of geometry #3 leads to highly nonlinear mechanical behavior (see Fig. B.10), which is not captured well in the simulations.

5.2. Parameter identification based on synthetic data

Since the homogenization theory assumes length scale separation and periodic boundary conditions in identifying the effective material parameters, it is important to understand the continuum behavior of the heterogeneous structures as the number of unit cells changes. For this, we apply the VFM described in Section 3.6 on the synthetic data to identify material parameters as the number of unit cells in each direction are varied simultaneously. Further, we also use synthetic data to identify parameters using multiple tests (as in the conventional approach). A discussion on this conventional approach is provided in Appendix A. The relative error is defined as

$$\text{LSE}_{\|\cdot\|_2} = \frac{\|\mathbf{C}_{\text{vec}}^{\text{H}} - \mathbf{C}_{\text{vec}}^{\text{M}}\|_2}{\|\mathbf{C}_{\text{vec}}^{\text{H}}\|_2} \quad \text{with } \mathbf{C}_{\text{vec}} \in \mathbb{R}^6, \quad (30)$$

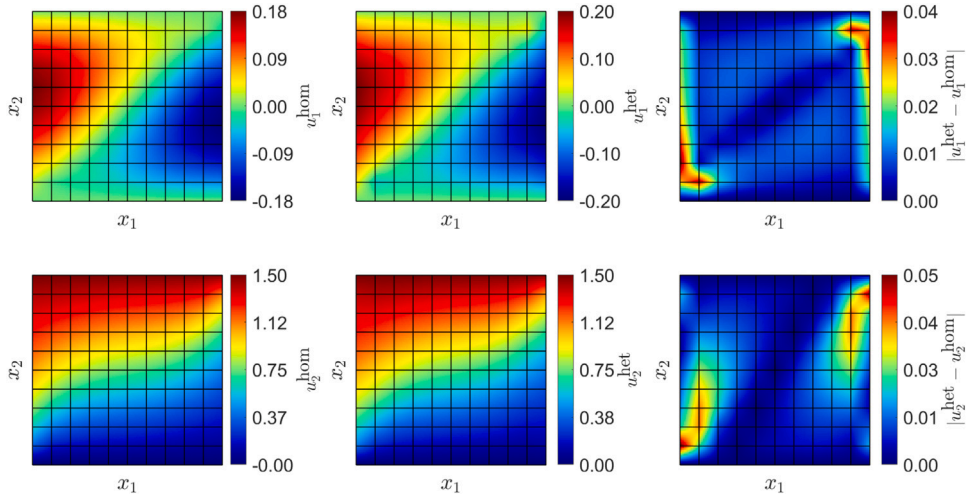


Fig. 4. Comparison between the displacement fields obtained from finite element simulations of a homogeneous specimen (left) and a heterogeneous structure made of geometry #1 (center). For the homogeneous specimen a finite element simulation using 10×10 bilinear quadrilateral elements was executed. The heterogeneous specimen was simulated using 1000×1000 bilinear quadrilateral elements. Afterwards, the displacement data at the unit cell corners were extracted and interpolated with a bilinear polynomial for each unit cell, to allow for a comparison with the homogeneous specimen. The difference between the fields is shown on the right.

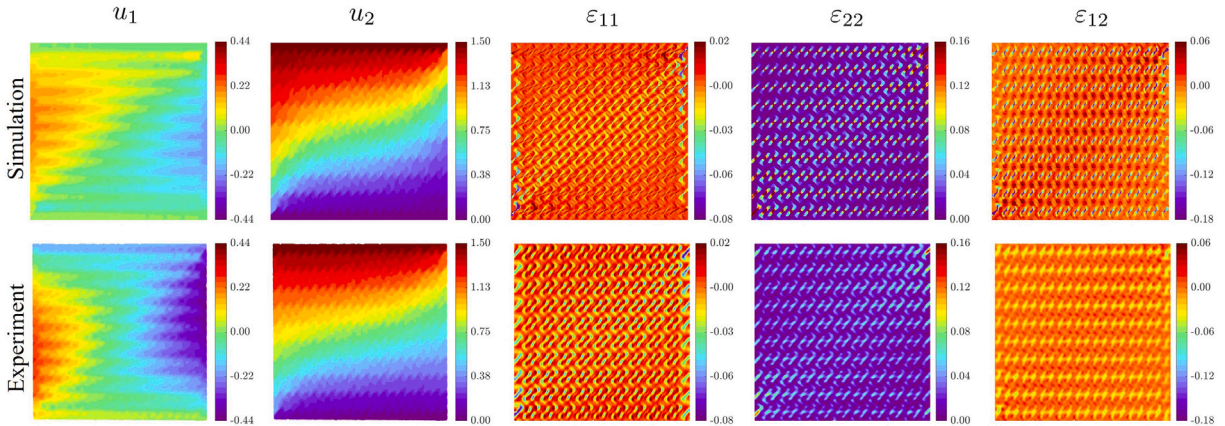


Fig. 5. Comparison between numerical (top) and experimentally measured (bottom) full-field displacement and strain field data for the 10 unit cell tessellation of geometry #1 subjected to displacement-controlled uniaxial tension test.

where C_{vec}^H is the vectorized homogenized stiffness tensor obtained from computational homogenization and C_{vec}^M is the vectorized stiffness tensor identified using the VFM and the conventional methods.

We compare the relative error in parameter identification when performing multiple tests (as in the conventional approach) and when using the VFM (Fig. 6). Since we exclude two rows and columns of boundary unit cells in the proposed VFM, the number of unit cells available to form the system of equations is guaranteed only when there are at least 7 unit cells in each direction and the results are shown starting with this number. For geometry #1, as the number of unit cells increases, the error calculated for the conventional method based on multiple tests decreases monotonically from 13.4% at 5 unit cell tessellation to 2.3% at 25 unit cell tessellation. Similarly, the error for the VFM decreases monotonically from 13.1% at 7 unit cell tessellation to 2.4% at 25 unit cell tessellation. This shows that the parameters identified using our VFM are as good as those obtained by performing multiple tests, as long as there are at least ten repeated unit cells in the domain of interest. We found this general conclusion to hold for most of the considered geometries. The only exception is geometry #3, for which the error remains at 7.0% (for multiple tests) and 11.8% (for the VFM) even beyond 10 unit cell tessellation. The comparatively large relative error, however, does not mean that all material parameters are inaccurately identified. By taking a closer look at the individual components of the stiffness tensor, it is observed that many of the parameters are identified with satisfactory accuracy. We show in Figs. S11 and S12 in the Supplementary Information the convergence behavior of all individual parameters for geometry #1 and geometry #3 as the number of unit cells for tessellation is varied, where we excluded the other geometries for brevity. While for geometry #1 all parameters are satisfactorily identified, in the case of geometry #3 a major portion of the error lies in just two of the parameters, i.e., C_{12} for multiple tests and C_{16} and C_{66}

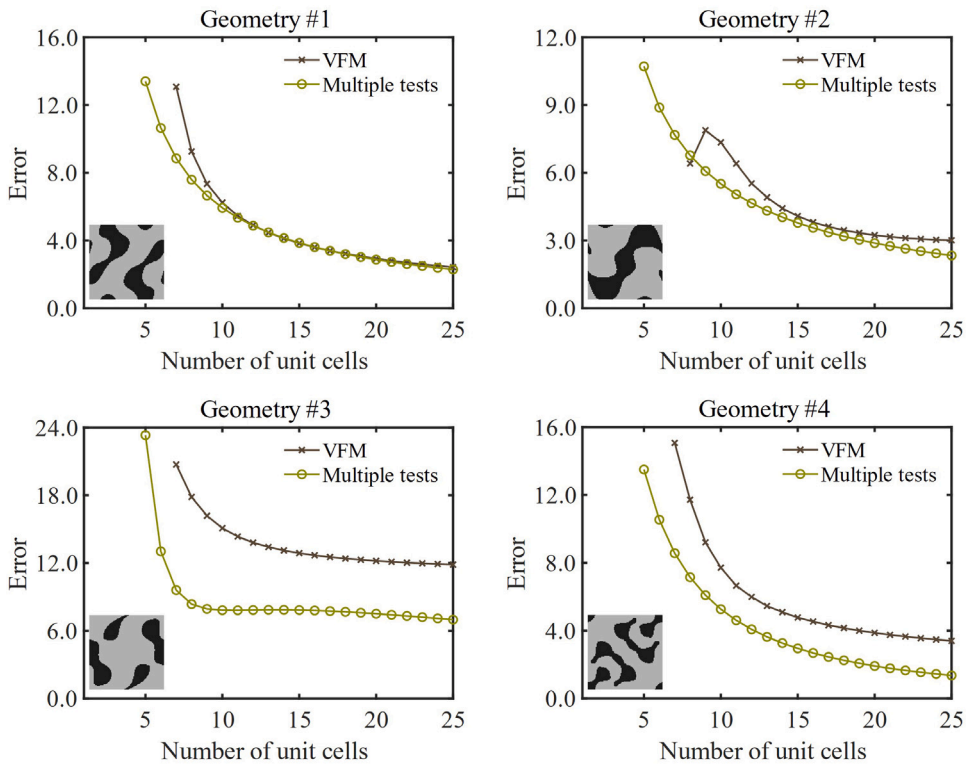


Fig. 6. Variation of least square error between homogenized stiffness tensor and stiffness tensor identified using the VFM and the conventional methods as the number of unit cells in each direction are varied.

Table 2

Comparison of stiffness tensor parameters identified for geometry #1 with 25 unit cell tessellation based on synthetic data using the VFM and the conventional methods against the computational homogenization.

Method	C_{11} (MPa)	C_{12} (MPa)	C_{22} (MPa)	C_{16} (MPa)	C_{26} (MPa)	C_{66} (MPa)
Homogenization	131.62	61.98	198.38	63.58	83.87	95.30
VFM	125.97	62.57	196.15	61.35	82.39	93.48
Multiple tests	129.86	67.93	199.37	64.01	85.47	95.54

for the VFM. Parameters C_{12} and C_{16} are quite small relative to the rest of the parameters and hence, they are hard to accurately estimate in comparison to the others. It can further be observed in Figs. S11 and S12 that for some of the parameters, the method of multiple tests outperforms the VFM, but for other parameters the VFM is superior. These results indicate that the parameters for geometry #3 are difficult to identify independently of the choice of the parameter identification method.

As the number of unit cells increases, the ratio of the number of unit cells along the boundary to the number of unit cells in the interior decreases. As a result, the boundary effects described in Section 5.1.1 diminish and the behavior of the structure approaches the continuum equivalent. In Table 2, we summarize the parameters identified for geometry #1 from both the methods in comparison to the homogenization for 25 unit cell tessellation (see Table B.3, Table B.4, Table B.5 for the other geometries).

5.3. Parameter identification based on experimental data

Fig. 7 summarizes the material parameters identified by the VFM using the simulated and experimental data for 10 unit cell tessellations in comparison to the homogenized stiffness. The parameters identified using synthetic data compare well with the homogenized properties for all the geometries. Further, a good qualitative agreement is observed for the parameters identified using experimental data. For some of the parameters, such as C_{12} , C_{22} , C_{16} , C_{26} , the experimentally determined parameters match the expectations quantitatively. In contrast, there is a larger discrepancy in the values of C_{11} , C_{66} , for almost all the geometries. These discrepancies are related to the fact that the experimentally measured displacement u_1 appears higher than in the simulations, i.e., about 0.1 mm, leading to an under-prediction of the stiffness in the lateral directions. An interesting observation is made for geometry #4. Based on the numerical data, we know that $C_{11} = C_{22}$ and $C_{16} = C_{26}$. However, we observe experimentally that $C_{11} < C_{22}$ and $C_{16} < C_{26}$. Geometry #3 has thin and sharp features in the softer phase. The presence of these sharp features inducing local stress singularities likely led to local material damage, which was subsequently observed as non-linear load–displacement

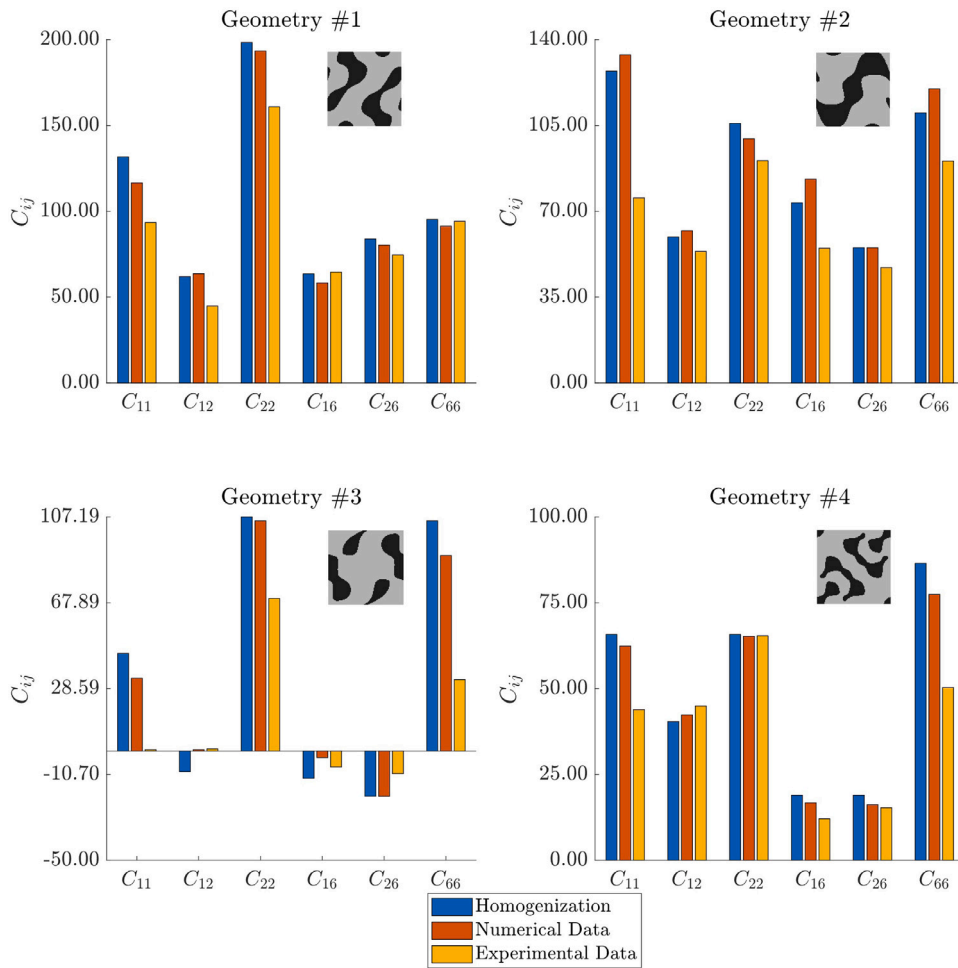


Fig. 7. Comparison of material parameters identified using the VFM from numerical and experimental data of 10 unit cell tessellations.

behavior (see Fig. B.10). As it is well known, the behavior of materials in the vicinity of such sharp discontinuities markedly deviates from a two-dimensional linear elastic continuum (Rosakis and Ravi-Chandar, 1986). Therefore, we attribute such non-linear behavior to the architecture of geometry #3 itself. In such micro-structures, our linear elastic model assumption fails.

We finalize the study by applying the Bayesian method described in Section 3.7 to the experimental data. The resulting marginal posterior probability distributions of the material parameters are shown in Fig. 8. It is observed that the computed mean values of the marginal posteriors are similar to the deterministic results shown in Fig. 7. Beyond that, the standard deviations of the marginal posteriors indicate (un)certainly in the parameter predictions. Matching our expectations, the parameter C_{22} is identified with the highest certainty, while for example, the identification of the parameter C_{11} shows a high uncertainty. An interesting observation is made for geometry #3. The parameters identified using synthetic data with the largest error are also the same parameters identified using experimental data with the largest standard deviation in the marginal posterior distribution. Additionally, it is noteworthy that the marginal posteriors of the parameters identified when the Bayesian method is applied to the numerical data show low standard deviations as the data is not affected by the experimental noise (see Fig. B.11).

We note that, for geometry #3, the marginal posterior probability distributions of the parameters exceed the thermodynamically admissible range, e.g., the marginal posterior of C_{11} is partially negative. This must be considered when interpreting the results. In this work, no measure was taken to enforce thermodynamic admissibility in the Bayesian method, which thus remains a future objective.

6. Conclusions

In this paper, we present an approach to identify the 6 independent elastic material parameters of plane anisotropic elasticity from a single experiment, using the virtual fields method. This approach allows for identifying shear-normal coupling parameters experimentally, a task that has remained challenging so far. We first demonstrate the effectiveness of our method using numerically

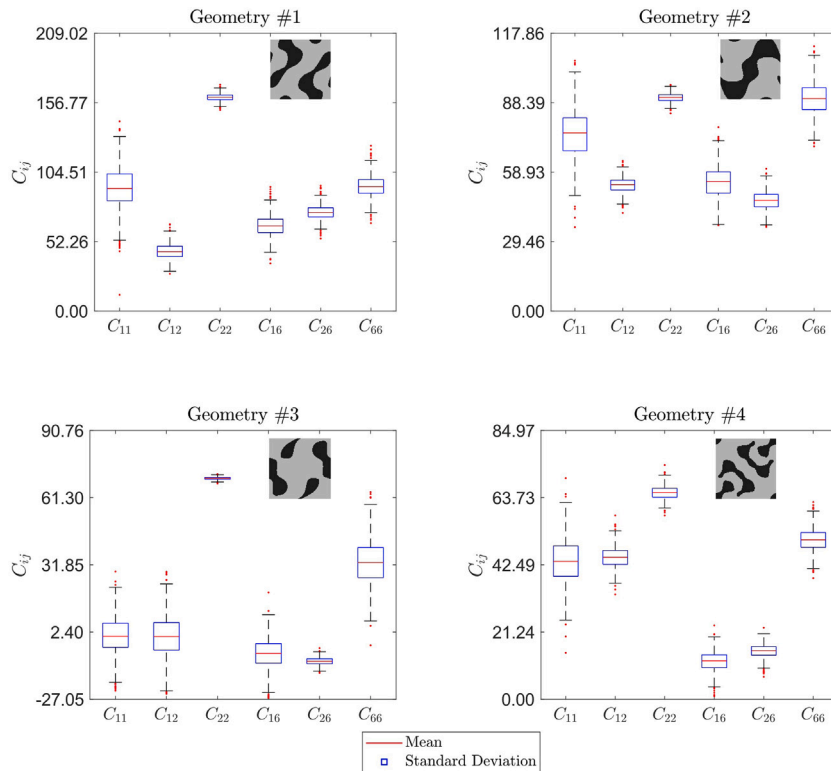


Fig. 8. Marginal posterior probability distributions of the material parameters obtained through Bayesian linear regression on the experimental data. The red lines indicate the mean of the marginal posterior distributions. The blue boxes indicate the standard deviation from the mean, i.e., the 68% probability interval. The black intervals indicate three times the standard deviation from the mean, i.e., the 99% probability interval.

generated data from a single tension test. We then experimentally validate the method on additively manufactured specimens, by measuring full-field displacement data and traction forces. We show that our method is effective for materials that include at least 10 repeated unit cells in their structure, to satisfy homogenization conditions. We calculate the uncertainty in the identification estimation of the material parameters using Bayesian linear regression. In the future, to further refine the experimental parameter identification, it is necessary to optimize the shape of the specimens to ensure strong contributions of strains from different stiffness tensor components. The proposed approach has the potential for measurements of elasticity parameters of complex, anisotropic, three-dimensional structured materials and composites with shear–shear couplings, and for the study of their nonlinear behavior. A further potential application of the method could be for parameter identification of constitutive tensors corresponding to different types of coupled behavior, such as generalized piezoelectric, flexoelectric, and piezomagnetic tensors.

CRedit authorship contribution statement

Jagannadh Boddapati: Conceptualization, Investigation, Software, Formal analysis, Writing – original draft. **Moritz Flaschel:** Conceptualization, Investigation, Software, Formal analysis, Writing – original draft. **Siddhant Kumar:** Conceptualization, Writing – review & editing. **Laura De Lorenzis:** Conceptualization, Writing – review & editing. **Chiara Daraio:** Conceptualization, Writing – review & editing, Supervision, Funding acquisition.

Declaration of competing interest

The authors declare that they have no known competing financial interests or personal relationships that could have appeared to influence the work reported in this paper.

Data availability

Data will be made available on request.

Acknowledgments

We would like to thank Prof. Fabrice Pierron (University of Southampton) for helpful discussions on the VFM and the DIC methods; Pierre Margerit (École Polytechnique) for helpful discussion on DIC; and Jihoon Ahn (Caltech) and Perry Samimy (Caltech) for their help in designing the experiments. C.D. and J.B. acknowledge support from the US National Science Foundation (NSF), grant number 1835735. M.F. and L.D.L. acknowledge support from the Swiss National Science Foundation (SNF), project number 200021_204316.

Appendix A. Parameter identification based on multiple tests

In this section, we explore a method of parameter identification that involves multiple tests (as in the conventional approach) in the context of anisotropic metamaterials. We subject the metamaterial to three different tests namely *Test A*, *Test B*, and *Test C* as shown in Fig. A.9. *Test A* and *Test C* are tension tests along x_2 and x_1 axis respectively, and *Test B* is a simple shear test. We assume that the average strains $\bar{\epsilon}_{ij}^{A,B,C}$ are known experimentally from full-field measurements. In addition, the reaction forces at the fixed end are known experimentally from load sensor measurements. We will show that the material parameters can be identified from the average strains and the net reaction forces from these three tests.

From Gauss’ divergence theorem, the average stresses $\bar{\sigma}$ are related to the tractions t at the fixed end as

$$t_i = \bar{\sigma}_{ij}n_j, \tag{A.1}$$

where n is the unit outward normal. For *Test A*, the unit outward normal n at the fixed end is $[0, -1]^T$. Using Eqs. (3) and (A.1), and assuming homogenized effective continuum behavior for the structured solid, we get

$$F_1^A / \mathcal{A} = \bar{\sigma}_6^A = C_{16}\bar{\epsilon}_1^A + C_{26}\bar{\epsilon}_2^A + C_{66}(2\bar{\epsilon}_6^A), \tag{A.2a}$$

$$F_2^A / \mathcal{A} = \bar{\sigma}_2^A = C_{12}\bar{\epsilon}_1^A + C_{22}\bar{\epsilon}_2^A + C_{26}(2\bar{\epsilon}_6^A), \tag{A.2b}$$

where $\bar{\sigma}_{12}^A, \bar{\sigma}_{22}^A$ are the average stress components, F_1^A, F_2^A are the reaction force components at the fixed end from *Test A* and \mathcal{A} is the cross sectional area of the fixed end.

Similarly, from *Test B* and *Test C*, we get

$$F_1^B / \mathcal{A} = \bar{\sigma}_6^B = C_{16}\bar{\epsilon}_1^B + C_{26}\bar{\epsilon}_2^B + C_{66}(2\bar{\epsilon}_6^B), \tag{A.3a}$$

$$F_2^B / \mathcal{A} = \bar{\sigma}_2^B = C_{12}\bar{\epsilon}_1^B + C_{22}\bar{\epsilon}_2^B + C_{26}(2\bar{\epsilon}_6^B), \tag{A.3b}$$

$$F_1^C / \mathcal{A} = \bar{\sigma}_1^C = C_{11}\bar{\epsilon}_1^C + C_{12}\bar{\epsilon}_2^C + C_{16}(2\bar{\epsilon}_6^C), \tag{A.3c}$$

$$F_2^C / \mathcal{A} = \bar{\sigma}_6^C = C_{16}\bar{\epsilon}_1^C + C_{26}\bar{\epsilon}_2^C + C_{66}(2\bar{\epsilon}_6^C). \tag{A.3d}$$

Rearranging Eqs. (A.2a), (A.2b) and (A.3a)–(A.3d) into a matrix form, we obtain a system of linear equations,

$$\begin{bmatrix} 0 & 0 & 2\bar{\epsilon}_6^A & \bar{\epsilon}_1^A & \bar{\epsilon}_2^A & 0 \\ 0 & \bar{\epsilon}_2^A & 0 & 0 & 2\bar{\epsilon}_6^A & \bar{\epsilon}_1^A \\ 0 & 0 & 2\bar{\epsilon}_6^B & \bar{\epsilon}_1^B & \bar{\epsilon}_2^B & 0 \\ 0 & \bar{\epsilon}_2^B & 0 & 0 & 2\bar{\epsilon}_6^B & \bar{\epsilon}_1^B \\ \bar{\epsilon}_1^C & 0 & 0 & 2\bar{\epsilon}_6^C & 0 & \bar{\epsilon}_2^C \\ 0 & 0 & 2\bar{\epsilon}_6^C & \bar{\epsilon}_1^C & \bar{\epsilon}_2^C & 0 \end{bmatrix} \begin{bmatrix} C_{11} \\ C_{22} \\ C_{66} \\ C_{16} \\ C_{26} \\ C_{12} \end{bmatrix} = \frac{1}{\mathcal{A}} \begin{bmatrix} F_1^A \\ F_2^A \\ F_1^B \\ F_2^B \\ F_1^C \\ F_2^C \end{bmatrix}. \tag{A.4}$$

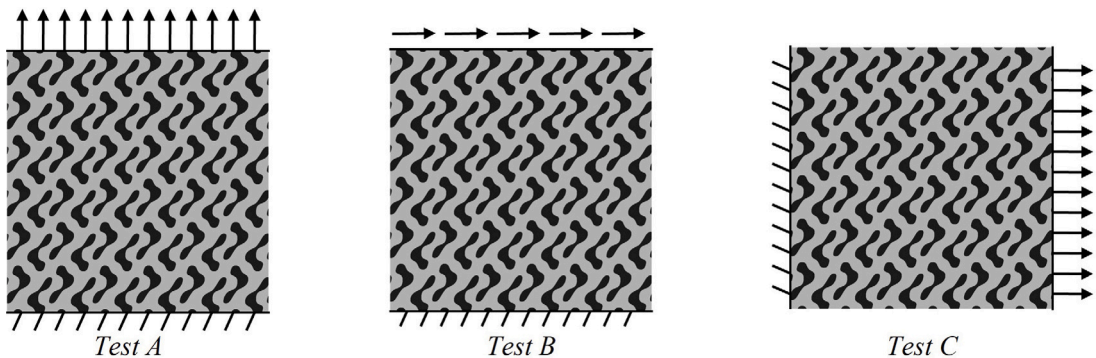


Fig. A.9. Parameter identification of an anisotropic metamaterial by performing three different tests.

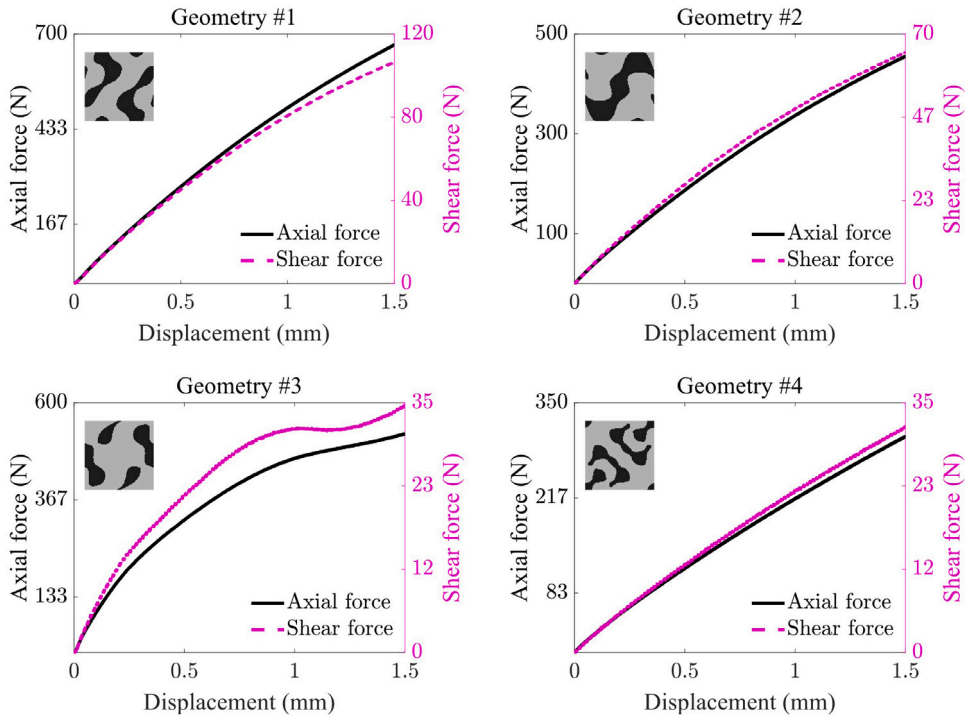


Fig. B.10. Axial and shear load–displacement data for all the experimentally tested specimens.

Table B.3

Comparison of stiffness tensor parameters identified for geometry #2 with 25 unit cell tessellation based on synthetic data using the VFM and the conventional methods against the computational homogenization.

Method	C_{11} (MPa)	C_{12} (MPa)	C_{22} (MPa)	C_{16} (MPa)	C_{26} (MPa)	C_{66} (MPa)
Homogenization	127.14	59.50	105.83	73.42	55.16	110.15
VFM	129.92	58.84	102.72	77.43	55.25	113.73
Multiple tests	123.82	57.44	102.35	72.74	54.68	110.12

For readability, Eq. (A.4) is written as

$$\mathcal{A}\bar{\epsilon}C_{\text{vec}} = F_{\text{vec}}, \tag{A.5}$$

where $\bar{\epsilon}$ is a non-symmetric square matrix of size 6 containing average strain components from all of the tests and F_{vec} is a vector containing net reaction force components from all of the tests. Then the material parameters $C_{\text{vec}}^{\text{opt}}$ can be obtained as a solution to the least squares minimization problem,

$$C_{\text{vec}}^{\text{opt}} = \arg \min_{C_{\text{vec}}} \|\mathcal{A}\bar{\epsilon}C_{\text{vec}} - F_{\text{vec}}\|^2. \tag{A.6}$$

It should be noted that we use this method for material parameter identification, only using the numerical data. We did not experimentally validate this method, since shear testing is non-trivial and requires dedicated setups, such as a hexapod machine (Dalemat, 2019).

Appendix B. Additional data

See Tables B.3–B.5 and Figs. B.10, B.11.

Appendix C. Supplementary data

Supplementary material related to this article can be found online at <https://doi.org/10.1016/j.jmps.2023.105471>.

Table B.4

Comparison of stiffness tensor parameters identified for geometry #3 with 25 unit cell tessellation based on synthetic data using the VFM and the conventional methods against the computational homogenization.

Method	C_{11} (MPa)	C_{12} (MPa)	C_{22} (MPa)	C_{16} (MPa)	C_{26} (MPa)	C_{66} (MPa)
Homogenization	44.70	-9.42	107.19	-12.52	-20.71	105.35
VFM	33.95	-5.84	106.48	-4.44	-20.78	92.65
Multiple tests	45.78	-19.27	112.01	-11.30	-20.30	105.65

Table B.5

Comparison of stiffness tensor parameters identified for geometry #4 with 25 unit cell tessellation based on synthetic data using the VFM and the conventional methods against the computational homogenization.

Method	C_{11} (MPa)	C_{12} (MPa)	C_{22} (MPa)	C_{16} (MPa)	C_{26} (MPa)	C_{66} (MPa)
Homogenization	65.74	40.36	65.74	18.95	18.95	86.47
VFM	65.45	40.94	65.43	17.93	17.76	82.19
Multiple tests	66.66	41.58	66.66	18.75	18.75	86.86

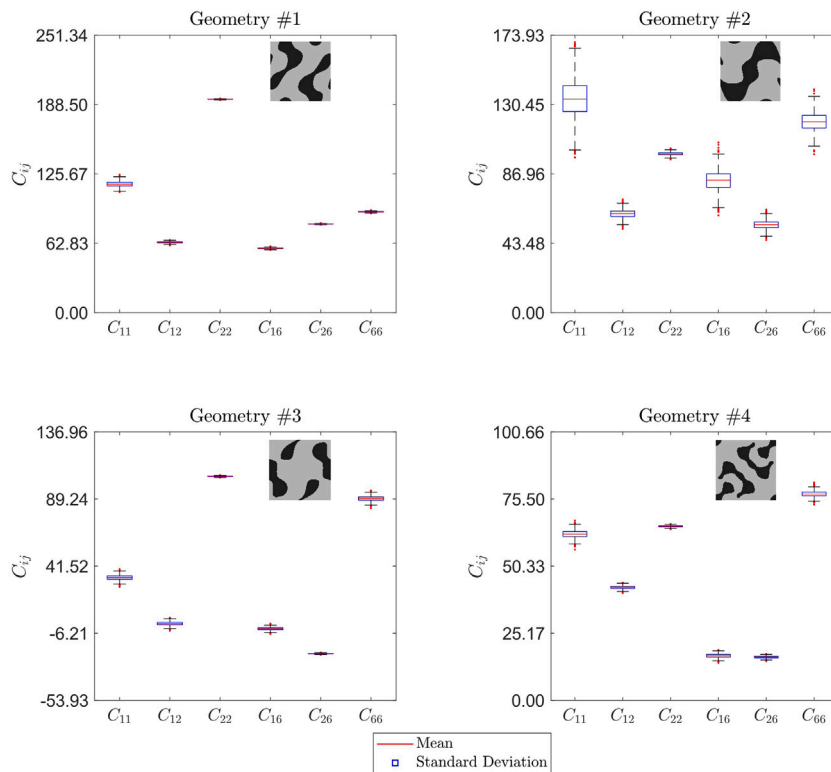


Fig. B.11. Marginal posterior probability distributions of the material parameters obtained through Bayesian linear regression on the numerical data.

References

Agnelli, F., Margerit, P., Celli, P., Daraio, C., Constantinescu, A., 2021. Systematic two-scale image analysis of extreme deformations in soft architected sheets. *Int. J. Mech. Sci.* 194, 106205. <http://dx.doi.org/10.1016/j.ijmecsci.2020.106205>, URL: <https://www.sciencedirect.com/science/article/pii/S0020740320343101>.

Agnelli, F., Nika, G., Constantinescu, A., 2022. Design of thin micro-architected panels with extension–bending coupling effects using topology optimization. *Comput. Methods Appl. Mech. Engrg.* 391, 114496. <http://dx.doi.org/10.1016/j.cma.2021.114496>, URL: <https://www.sciencedirect.com/science/article/pii/S0045782521007040>.

Ahn, Y.K., Lee, H.J., Kim, Y.Y., 2017. Conical refraction of elastic waves by anisotropic metamaterials and application for parallel translation of elastic waves. *Sci. Rep.* 7 (1), 10072. <http://dx.doi.org/10.1038/s41598-017-10691-6>, URL: <http://www.nature.com/articles/s41598-017-10691-6>.

Andreassen, E., Andreasen, C.S., 2014. How to determine composite material properties using numerical homogenization. *Comput. Mater. Sci.* 83, 488–495. <http://dx.doi.org/10.1016/j.commatsci.2013.09.006>, URL: <https://www.sciencedirect.com/science/article/pii/S0927025613005302>.

Andreas, U., dell’Isola, F., Giorgio, I., Placidi, L., Lekszycki, T., Rizzi, N.L., 2016. Numerical simulations of classical problems in two-dimensional (non) linear second gradient elasticity. *Internat. J. Engrg. Sci.* 108, 34–50. <http://dx.doi.org/10.1016/j.ijengsci.2016.08.003>, URL: <https://linkinghub.elsevier.com/retrieve/pii/S0020722516308187>.

Auffray, N., Ropars, P., 2016. Invariant-based reconstruction of bidimensional elasticity tensors. *Int. J. Solids Struct.* 87, 183–193. <http://dx.doi.org/10.1016/j.ijsolstr.2016.02.013>, URL: <https://linkinghub.elsevier.com/retrieve/pii/S0020768316000676>.

- Avril, S., Bonnet, M., Bretelle, A.S., Grédiac, M., Hild, F., Ienny, P., Latourte, F., Lemosse, D., Pagano, S., Pagnacco, E., Pierron, F., 2008. Overview of identification methods of mechanical parameters based on full-field measurements. *Exp. Mech.* 48 (4), 381–402. <http://dx.doi.org/10.1007/s11340-008-9148-y>, URL: <http://link.springer.com/10.1007/s11340-008-9148-y>.
- Avril, S., Grédiac, M., Pierron, F., 2004. Sensitivity of the virtual fields method to noisy data. *Comput. Mech.* 34 (6), 439–452. <http://dx.doi.org/10.1007/s00466-004-0589-6>.
- Bastek, J.H., Kumar, S., Telgen, B., Glaesener, R.N., Kochmann, D.M., 2022. Inverting the structure–property map of truss metamaterials by deep learning. *Proc. Natl. Acad. Sci.* 119 (1), e2111505119. <http://dx.doi.org/10.1073/pnas.2111505119>, URL: <https://www.pnas.org/doi/abs/10.1073/pnas.2111505119>, Publisher: Proceedings of the National Academy of Sciences.
- Bertoldi, K., Vitelli, V., Christensen, J., van Hecke, M., 2017. Flexible mechanical metamaterials. *Nat. Rev. Mater.* 2 (11), 1–11. <http://dx.doi.org/10.1038/natrevmats.2017.66>, URL: <https://www.nature.com/articles/natrevmats201766>, Number: 11 Publisher: Nature Publishing Group.
- Besnard, G., Hild, F., Roux, S., 2006. “Finite-element” displacement fields analysis from digital images: Application to Portevin–Le Châtelier bands. *Exp. Mech.* 46 (6), 789–803. <http://dx.doi.org/10.1007/s11340-006-9824-8>.
- Blaysat, B., Neggiers, J., Grédiac, M., Sur, F., 2020. Towards criteria characterizing the metrological performance of full-field measurement techniques. *Exp. Mech.* 60 (3), 393–407. <http://dx.doi.org/10.1007/s11340-019-00566-4>.
- Cahn, J.W., 1965. Phase separation by spinodal decomposition in isotropic systems. *J. Chem. Phys.* 42 (1), 93–99. <http://dx.doi.org/10.1063/1.1695731>, URL: <https://aip.scitation.org/doi/10.1063/1.1695731>, Publisher: American Institute of Physics.
- Chen, W., Ruan, D., Huang, X., 2018. Optimization for twist chirality of structural materials induced by axial strain. *Mater. Today Commun.* 15, 175–184. <http://dx.doi.org/10.1016/j.mtcomm.2018.03.010>, URL: <https://www.sciencedirect.com/science/article/pii/S235249281830031X>.
- Christensen, J., Kadic, M., Wegener, M., Kraft, O., Wegener, M., 2015. Vibrant times for mechanical metamaterials. *MRS Commun.* 5 (3), 453–462. <http://dx.doi.org/10.1557/mrc.2015.51>, URL: <http://link.springer.com/10.1557/mrc.2015.51>.
- Considine, J., Pierron, F., Turner, K., Vahey, D., 2014. General anisotropy identification of paperboard with virtual fields method. *Exp. Mech.* 54 (8), 1395–1410. <http://dx.doi.org/10.1007/s11340-014-9903-1>.
- Dalemat, M., 2019. Une expérimentation réussie pour l'identification de la réponse mécanique sans loi de comportement : Approche data-driven appliquée aux membranes élastomères, No. 2019ECDN0065 (Theses). École centrale de Nantes, URL: <https://tel.archives-ouvertes.fr/tel-02506891>.
- Dos Reis, F., Karathanasopoulos, N., 2022. Inverse metamaterial design combining genetic algorithms with asymptotic homogenization schemes. *Int. J. Solids Struct.* 250, 111702. <http://dx.doi.org/10.1016/j.ijsolstr.2022.111702>, URL: <https://www.sciencedirect.com/science/article/pii/S0020768322002104>.
- Every, A.G., Sachse, W., 1990. Determination of the elastic constants of anisotropic solids from acoustic-wave group-velocity measurements. *Phys. Rev. B* 42 (13), 8196–8205. <http://dx.doi.org/10.1103/PhysRevB.42.8196>, URL: <https://link.aps.org/doi/10.1103/PhysRevB.42.8196>, Publisher: American Physical Society.
- Fischer, P., Klassen, M., Mergheim, J., Steinmann, P., Müller, R., 2011. Isogeometric analysis of 2D gradient elasticity. *Comput. Mech.* 47 (3), 325–334. <http://dx.doi.org/10.1007/s00466-010-0543-8>, URL: <http://link.springer.com/10.1007/s00466-010-0543-8>.
- Flaschel, M., 2023. Automated Discovery of Material Models in Continuum Solid Mechanics (Ph.D. thesis). ETH Zurich, <http://dx.doi.org/10.3929/ETHZ-B-000602750>, URL: <http://hdl.handle.net/20.500.11850/602750>.
- Flaschel, M., Kumar, S., De Lorenzis, L., 2021. Unsupervised discovery of interpretable hyperelastic constitutive laws. *Comput. Methods Appl. Mech. Engrg.* 381, 113852. <http://dx.doi.org/10.1016/j.cma.2021.113852>.
- Flaschel, M., Kumar, S., De Lorenzis, L., 2022. Discovering plasticity models without stress data. *npj Comput. Mater.* 8 (1), 91. <http://dx.doi.org/10.1038/s41524-022-00752-4>, URL: <https://www.nature.com/articles/s41524-022-00752-4>.
- Flaschel, M., Kumar, S., De Lorenzis, L., 2023. Automated discovery of generalized standard material models with EUCLID. *Comput. Methods Appl. Mech. Engrg.* 405, 115867. <http://dx.doi.org/10.1016/j.cma.2022.115867>, URL: <https://linkinghub.elsevier.com/retrieve/pii/S0045782522008234>.
- Forté, S., Vianello, M., 2014. A unified approach to invariants of plane elasticity tensors. *Meccanica* 49 (9), 2001–2012. <http://dx.doi.org/10.1007/s11012-014-9916-y>, URL: <http://link.springer.com/10.1007/s11012-014-9916-y>.
- François, M., Geymonat, G., Berthaud, Y., 1998. Determination of the symmetries of an experimentally determined stiffness tensor: Application to acoustic measurements. *Int. J. Solids Struct.* 35 (31), 4091–4106. [http://dx.doi.org/10.1016/S0020-7683\(97\)00303-X](http://dx.doi.org/10.1016/S0020-7683(97)00303-X), URL: <https://www.sciencedirect.com/science/article/pii/S002076839700303X>.
- Frenzel, T., Kadic, M., Wegener, M., 2017. Three-dimensional mechanical metamaterials with a twist. *Science* 358 (6366), 1072–1074. <http://dx.doi.org/10.1126/science.aao4640>, URL: <https://www.sciencemag.org/lookup/doi/10.1126/science.aao4640>.
- Gras, R., Leclerc, H., Hild, F., Roux, S., Schneider, J., 2015. Identification of a set of macroscopic elastic parameters in a 3D woven composite: Uncertainty analysis and regularization. *Int. J. Solids Struct.* 55, 2–16. <http://dx.doi.org/10.1016/j.ijsolstr.2013.12.023>, URL: <https://www.sciencedirect.com/science/article/pii/S0020768313004964>.
- Greaves, G.N., Greer, A.L., Lakes, R.S., Rouxel, T., 2011. Poisson's ratio and modern materials. *Nature Mater.* 10 (11), 823–837. <http://dx.doi.org/10.1038/nmat3134>, URL: <https://www.nature.com/articles/nmat3134>, Number: 11 Publisher: Nature Publishing Group.
- Grédiac, M., 1989. Principle of virtual work and identification. *Comptes Rendus de L Academie des Sciences Serie Ii* (309(1)), 1–5.
- Grédiac, M., Pierron, F., 2006. Applying the Virtual Fields Method to the identification of elasto-plastic constitutive parameters. *Int. J. Plast.* 22 (4), 602–627. <http://dx.doi.org/10.1016/j.ijplas.2005.04.007>, URL: <https://linkinghub.elsevier.com/retrieve/pii/S0749641905000896>.
- Grédiac, M., Pierron, F., Avril, S., Toussaint, E., 2008. The Virtual Fields Method for extracting constitutive parameters from full-field measurements: a review. *Strain* 42 (4), 233–253. <http://dx.doi.org/10.1111/j.1475-1305.2006.tb01504.x>, URL: <http://doi.wiley.com/10.1111/j.1475-1305.2006.tb01504.x>.
- Guseinov, R., McMahan, C., Pérez, J., Daraio, C., Bickel, B., 2020. Programming temporal morphing of self-actuated shells. *Nature Commun.* 11 (1), 237. <http://dx.doi.org/10.1038/s41467-019-14015-2>, URL: <https://www.nature.com/articles/s41467-019-14015-2>, Number: 1 Publisher: Nature Publishing Group.
- Hild, F., Roux, S., 2012. Comparison of local and global approaches to digital image correlation. *Exp. Mech.* 52 (9), 1503–1519. <http://dx.doi.org/10.1007/s11340-012-9603-7>, URL: <http://link.springer.com/10.1007/s11340-012-9603-7>.
- Huang, D.Z., Xu, K., Farhat, C., Darve, E., 2020. Learning constitutive relations from indirect observations using deep neural networks. *J. Comput. Phys.* 416, 109491. <http://dx.doi.org/10.1016/j.jcp.2020.109491>, URL: <https://linkinghub.elsevier.com/retrieve/pii/S0021999120302655>.
- Joshi, A., Thakolkaran, P., Zheng, Y., Escande, M., Flaschel, M., De Lorenzis, L., Kumar, S., 2022. Bayesian-EUCLID: Discovering hyperelastic material laws with uncertainties. *Comput. Methods Appl. Mech. Engrg.* 398, 115225. <http://dx.doi.org/10.1016/j.cma.2022.115225>, URL: <https://linkinghub.elsevier.com/retrieve/pii/S0045782522003681>.
- Kadic, M., Bückmann, T., Stenger, N., Thiel, M., Wegener, M., 2012. On the practicability of pentamode mechanical metamaterials. *Appl. Phys. Lett.* 100 (19), 191901. <http://dx.doi.org/10.1063/1.4709436>, URL: <https://aip.scitation.org/doi/10.1063/1.4709436>, Publisher: American Institute of Physics.
- Kaina, N., Lemoult, F., Fink, M., Lerosey, G., 2015. Negative refractive index and acoustic superlens from multiple scattering in single negative metamaterials. *Nature* 525 (7567), 77–81. <http://dx.doi.org/10.1038/nature14678>, URL: <https://www.nature.com/articles/nature14678>, Number: 7567 Publisher: Nature Publishing Group.
- Karathanasopoulos, N., Dos Reis, F., Diamantopoulou, M., Ganghoffer, J.F., 2020. Mechanics of beams made from chiral metamaterials: Tuning deflections through normal-shear strain couplings. *Mater. Des.* 189, 108520. <http://dx.doi.org/10.1016/j.matdes.2020.108520>, URL: <https://www.sciencedirect.com/science/article/pii/S0264127520300538>.
- Kim, J.H., Barlat, F., Pierron, F., Lee, M.G., 2014. Determination of anisotropic plastic constitutive parameters using the Virtual Fields Method. *Exp. Mech.* 54 (7), 1189–1204. <http://dx.doi.org/10.1007/s11340-014-9879-x>.

- Kim, C., Kim, J.H., Lee, M.G., 2020. A virtual fields method for identifying anisotropic elastic constants of fiber reinforced composites using a single tension test: Theory and validation. *Composites B* 200, 108338. <http://dx.doi.org/10.1016/j.compositesb.2020.108338>, URL: <https://www.sciencedirect.com/science/article/pii/S1359836820333874>.
- Kulagin, R., Beygelzimer, Y., Estrin, Y., Schumilin, A., Gumbsch, P., 2020. Architected lattice materials with tunable anisotropy: Design and analysis of the material property space with the aid of machine learning. *Adv. Eng. Mater.* 22 (12), 2001069. <http://dx.doi.org/10.1002/adem.202001069>, URL: <https://onlinelibrary.wiley.com/doi/10.1002/adem.202001069>.
- Kumar, S., Tan, S., Zheng, L., Kochmann, D.M., 2020. Inverse-designed spinodoid metamaterials. *npj Comput. Mater.* 6 (1), <http://dx.doi.org/10.1038/s41524-020-0341-6>.
- Lee, H.J., Lee, H.S., Ma, P.S., Kim, Y.Y., 2016. Effective material parameter retrieval of anisotropic elastic metamaterials with inherent nonlocality. *J. Appl. Phys.* 120 (10), 104902. <http://dx.doi.org/10.1063/1.4962274>, URL: <https://aip.scitation.org/doi/10.1063/1.4962274>, Publisher: American Institute of Physics.
- Lee, H.J., Singer, J.P., Thomas, E.L., 2012. Micro-/nanostuctured mechanical metamaterials. *Adv. Mater.* 24 (36), 4782–4810. <http://dx.doi.org/10.1002/adma.201201644>, URL: <https://onlinelibrary.wiley.com/doi/abs/10.1002/adma.201201644>, eprint: <https://onlinelibrary.wiley.com/doi/pdf/10.1002/adma.201201644>.
- Liu, X., Tao, F., Du, H., Yu, W., Xu, K., 2020. Learning nonlinear constitutive laws using neural network models based on indirectly measurable data. *J. Appl. Mech.* 87 (8), 081003. <http://dx.doi.org/10.1115/1.4047036>, URL: <https://asmedigitalcollection.asme.org/appliedmechanics/article/doi/10.1115/1.4047036/1083320/Learning-Nonlinear-Constitutive-Laws-Using-Neural>.
- Man, H., Furukawa, T., 2011. Neural network constitutive modelling for non-linear characterization of anisotropic materials. *Internat. J. Numer. Methods Engrg.* 85 (8), 939–957. <http://dx.doi.org/10.1002/nme.2999>, URL: <https://onlinelibrary.wiley.com/doi/10.1002/nme.2999>.
- Mao, H., Rumpfer, R., Gaborit, M., Göransson, P., Kennedy, J., O'Connor, D., Trimble, D., Rice, H., 2020. Twist, tilt and stretch: From isometric Kelvin cells to anisotropic cellular materials. *Mater. Des.* 193, 108855. <http://dx.doi.org/10.1016/j.matdes.2020.108855>, URL: <https://linkinghub.elsevier.com/retrieve/pii/S0264127520303890>.
- Marek, A., Davis, F.M., Pierron, F., 2017. Sensitivity-based virtual fields for the non-linear virtual fields method. *Comput. Mech.* 60 (3), 409–431. <http://dx.doi.org/10.1007/s00466-017-1411-6>, URL: <http://link.springer.com/10.1007/s00466-017-1411-6>.
- Marino, E., Flaschel, M., Kumar, S., De Lorenzis, L., 2023. Automated identification of linear viscoelastic constitutive laws with EUCLID. *Mech. Mater.* 181, 104643. <http://dx.doi.org/10.1016/j.mechmat.2023.104643>, URL: <https://linkinghub.elsevier.com/retrieve/pii/S0167663623000893>.
- Milton, G.W., Cherkav, A.V., 1995. Which elasticity tensors are realizable? *J. Eng. Mater. Technol.* 117 (4), 483–493. <http://dx.doi.org/10.1115/1.2804743>.
- Mindlin, R.D., Eshel, N.N., 1968. On first strain-gradient theories in linear elasticity. *Int. J. Solids Struct.* 4 (1), 109–124. [http://dx.doi.org/10.1016/0020-7683\(68\)90036-X](http://dx.doi.org/10.1016/0020-7683(68)90036-X), URL: <https://www.sciencedirect.com/science/article/pii/002076836890036X>.
- Ni, X., Guo, X., Li, J., Huang, Y., Zhang, Y., Rogers, J.A., 2019. 2D mechanical metamaterials with widely tunable unusual modes of thermal expansion. *Adv. Mater.* 31 (48), 1905405. <http://dx.doi.org/10.1002/adma.201905405>, URL: <https://onlinelibrary.wiley.com/doi/abs/10.1002/adma.201905405>, eprint: <https://onlinelibrary.wiley.com/doi/pdf/10.1002/adma.201905405>.
- Pierron, F., 2023. Material testing 2.0: A brief review. *Strain* e12434. <http://dx.doi.org/10.1111/str.12434>, URL: <https://onlinelibrary.wiley.com/doi/abs/10.1111/str.12434>.
- Pierron, F., Avril, S., Tran, V.T., 2010. Extension of the virtual fields method to elasto-plastic material identification with cyclic loads and kinematic hardening. *Int. J. Solids Struct.* 47 (22), 2993–3010. <http://dx.doi.org/10.1016/j.ijsolstr.2010.06.022>, URL: <https://www.sciencedirect.com/science/article/pii/S002076831000243X>.
- Pierron, F., Grédiac, M., 2012. *The Virtual Fields Method*. Springer New York, New York, NY, <http://dx.doi.org/10.1007/978-1-4614-1824-5>, URL: <http://link.springer.com/10.1007/978-1-4614-1824-5>.
- Podestá, J., Méndez, C., Toro, S., Huespe, A., 2019. Symmetry considerations for topology design in the elastic inverse homogenization problem. *J. Mech. Phys. Solids* 128, 54–78. <http://dx.doi.org/10.1016/j.jmps.2019.03.018>, URL: <https://linkinghub.elsevier.com/retrieve/pii/S0022509618305210>.
- Promma, N., Raka, B., Grédiac, M., Toussaint, E., Le Cam, J.B., Balandraud, X., Hild, F., 2009. Application of the virtual fields method to mechanical characterization of elastomeric materials. *Int. J. Solids Struct.* 46 (3), 698–715. <http://dx.doi.org/10.1016/j.ijsolstr.2008.09.025>, URL: <https://www.sciencedirect.com/science/article/pii/S0020768308003946>.
- Risso, G., Sakovsky, M., Ermanni, P., 2021. Instability-driven shape forming of fiber reinforced polymer frames. *Compos. Struct.* 268, 113946. <http://dx.doi.org/10.1016/j.compstruct.2021.113946>, URL: <https://www.sciencedirect.com/science/article/pii/S02638223211004062>.
- Rosakis, A.J., Ravi-Chandar, K., 1986. On crack-tip stress state: An experimental evaluation of three-dimensional effects. *Int. J. Solids Struct.* 22 (2), 121–134. [http://dx.doi.org/10.1016/0020-7683\(86\)90002-8](http://dx.doi.org/10.1016/0020-7683(86)90002-8), URL: <https://www.sciencedirect.com/science/article/pii/0020768386900028>.
- Rossi, M., Lava, P., Pierron, F., Debruyne, D., Sasso, M., 2015. Effect of DIC spatial resolution, noise and interpolation error on identification results with the VFM. *Strain* 51 (3), 206–222. <http://dx.doi.org/10.1111/str.12134>, URL: <https://onlinelibrary.wiley.com/doi/abs/10.1111/str.12134>, eprint: <https://onlinelibrary.wiley.com/doi/pdf/10.1111/str.12134>.
- Roux, S., Hild, F., 2020. Optimal procedure for the identification of constitutive parameters from experimentally measured displacement fields. *Int. J. Solids Struct.* 184, 14–23. <http://dx.doi.org/10.1016/j.ijsolstr.2018.11.008>, URL: <https://linkinghub.elsevier.com/retrieve/pii/S0020768318304542>.
- Rychlewski, J., 1984. On Hooke's law. *J. Appl. Math. Mech.* 48 (3), 303–314. [http://dx.doi.org/10.1016/0021-8928\(84\)90137-0](http://dx.doi.org/10.1016/0021-8928(84)90137-0), URL: <https://www.sciencedirect.com/science/article/pii/0021892884901370>.
- Schittny, R., Bückmann, T., Kadic, M., Wegener, M., 2013. Elastic measurements on macroscopic three-dimensional pentamode metamaterials. *Appl. Phys. Lett.* 103 (23), 231905. <http://dx.doi.org/10.1063/1.4838663>, URL: <https://aip.scitation.org/doi/10.1063/1.4838663>, Publisher: American Institute of Physics.
- Soyarslan, C., Bargmann, S., Pradas, M., Weissmüller, J., 2018. 3D stochastic bicontinuous microstructures: Generation, topology and elasticity. *Acta Mater.* 149, 326–340. <http://dx.doi.org/10.1016/j.actamat.2018.01.005>.
- Surjadi, J.U., Gao, L., Du, H., Li, X., Xiong, X., Fang, N.X., Lu, Y., 2019. Mechanical metamaterials and their engineering applications. *Adv. Eng. Mater.* 21 (3), 1800864. <http://dx.doi.org/10.1002/adem.201800864>, URL: <https://onlinelibrary.wiley.com/doi/abs/10.1002/adem.201800864>, eprint: <https://onlinelibrary.wiley.com/doi/pdf/10.1002/adem.201800864>.
- Sutton, M.A., Orteu, J.J., Schreier, H., 2009. *Image Correlation for Shape, Motion and Deformation Measurements: Basic Concepts, Theory and Applications*. Springer Science & Business Media.
- Thakolkaran, P., Joshi, A., Zheng, Y., Flaschel, M., De Lorenzis, L., Kumar, S., 2022. NN-EUCLID: Deep-learning hyperelasticity without stress data. *J. Mech. Phys. Solids* 169, 105076. <http://dx.doi.org/10.1016/j.jmps.2022.105076>, URL: <https://linkinghub.elsevier.com/retrieve/pii/S0022509622002538>.
- Tibshirani, R., 1996. Regression shrinkage and selection via the Lasso. *J. R. Stat. Soc. Ser. B Stat. Methodol.* 58 (1), 267–288. <http://dx.doi.org/10.1111/j.2517-6161.1996.tb02080.x>, URL: <http://doi.wiley.com/10.1111/j.2517-6161.1996.tb02080.x>.
- Ting, Chi-Tsai, T., 1996. *Anisotropic Elasticity: Theory and Applications*, No. 45. Oxford University Press on Demand.
- Wu, W., Hu, W., Qian, G., Liao, H., Xu, X., Berto, F., 2019. Mechanical design and multifunctional applications of chiral mechanical metamaterials: A review. *Mater. Des.* 180, 107950. <http://dx.doi.org/10.1016/j.matdes.2019.107950>, URL: <https://www.sciencedirect.com/science/article/pii/S0264127519303880>.
- Yang, X., Kweun, M., Kim, Y.Y., 2019. Monolayer metamaterial for full mode-converting transmission of elastic waves. *Appl. Phys. Lett.* 115 (7), 071901. <http://dx.doi.org/10.1063/1.5109758>, URL: <https://aip.scitation.org/doi/10.1063/1.5109758>, Publisher: American Institute of Physics.
- Yang, H., Timofeev, D., Abali, B.E., Li, B., Müller, W.H., 2021. Verification of strain gradient elasticity computation by analytical solutions. *ZAMM Z. Angew. Math. Mech.* <http://dx.doi.org/10.1002/zamm.202100023>, URL: <https://onlinelibrary.wiley.com/doi/10.1002/zamm.202100023>.

- Yuan, Z., Cui, Z., Ju, J., 2021. Micropolar homogenization of wavy tetra-chiral and tetra-achiral lattices to identify axial–shear coupling and directional negative Poisson’s ratio. *Mater. Des.* 201, 109483. <http://dx.doi.org/10.1016/j.matdes.2021.109483>, URL: <https://www.sciencedirect.com/science/article/pii/S0264127521000368>.
- Zadpoor, A.A., 2016. Mechanical meta-materials. *Mater. Horiz.* 3 (5), 371–381. <http://dx.doi.org/10.1039/C6MH00065G>, URL: <http://xlink.rsc.org/?DOI=C6MH00065G>.
- Zheng, M., Liu, X., Chen, Y., Miao, H., Zhu, R., Hu, G., 2019. Theory and realization of nonresonant anisotropic singly polarized solids carrying only shear waves. *Phys. Rev. A* 12 (1), 014027. <http://dx.doi.org/10.1103/PhysRevApplied.12.014027>, URL: <https://link.aps.org/doi/10.1103/PhysRevApplied.12.014027>, Publisher: American Physical Society.
- Zheng, M., Park, C.I., Liu, X., Zhu, R., Hu, G., Kim, Y.Y., 2020. Non-resonant metasurface for broadband elastic wave mode splitting. *Appl. Phys. Lett.* 116 (17), 171903. <http://dx.doi.org/10.1063/5.0005408>, URL: <https://aip.scitation.org/doi/10.1063/5.0005408>, Publisher: American Institute of Physics.